

Node-Dependent Kinematics Approach for Damage Analysis of Reinforced Concrete Structures

Jiahui Shen¹; Mário Rui Arruda²; Alfonso Pagani³; Erasmo Carrera⁴;
Enrico Zappino⁵; Riccardo Augello⁶; and Marco Petrolo⁷

Abstract: Modeling damage behavior in engineering structures is vital, but balancing computational efficiency and accuracy presents a significant challenge. This study introduces an advanced higher-order beam model incorporating a node-dependent kinematics approach, enhancing the efficiency of damage analysis in reinforced concrete structures. The proposed beam model is built in the framework of Carrera Unified Formulation, enabling a three-dimensional displacement field from a one-dimensional beam model via variable cross-sectional expansion functions. The node-dependent kinematics approach allows diverse cross-sectional kinematics at different nodes on the same beam element. Therefore, a customized approach can be applied where critical areas susceptible to localized damage utilize Lagrange polynomials and a Component-Wise approach for detailed analysis, while noncritical zones apply lower-order Taylor polynomials to reduce computational resources. The model incorporates a modified Mazars damage model for concrete and von Mises plasticity for steel. Four numerical assessments show that the proposed beam model with node-dependent kinematics can maintain accuracy while reducing degrees of freedom by 35%–60% compared to fully refined models with Lagrange polynomials. Moreover, the node-dependent kinematics only require simple adjustments to the cross-sectional kinematics as necessary without extensive mesh refinement. This scalability significantly simplifies the tuning process of beam models for practical applications. DOI: [10.1061/JSENDH.STENG-13729](https://doi.org/10.1061/JSENDH.STENG-13729). © 2025 American Society of Civil Engineers.

Introduction

Over the past few decades, numerous numerical models have been developed for the structural analysis of reinforced concrete (RC) structures. Experimental studies (MacGregor et al. 1997) have revealed that RC structures exhibit complex behavior, including concrete cracking and crushing, steel plasticity, and the bond-slip interaction between steel rebars and concrete. Capturing these phenomena in a numerical method demands significant computational resources. Despite the challenges posed by computational

requirements, numerical models are still essential in specialized engineering and for conducting parametric studies (Kadhim et al. 2020), which provides a cost-efficient alternative to experimental testing. The crucial aspect of simulating RC structures is choosing appropriate material representations for concrete and steel according to specific application scenarios. In addition, accurately modeling the interaction between concrete and steel reinforcement remains a significant and ongoing challenge (Ogura et al. 2008).

Currently, two principal approaches (Maekawa et al. 2003) are widely utilized in the simulation of RC structures: the continuum method using three-dimensional (3D) finite-element analysis (FEA) and the frame modeling method. The FEA with continuum method uses 3D solid elements to model concrete, whereas steel rebars are simulated using one-dimensional (1D) beam or truss elements (Earij et al. 2017; Sinaei et al. 2012). Various plasticity theories are applied to capture the behavior of steel rebars (de Souza Neto et al. 2011). Continuum damage models, both isotropic (Mazars 1984) and anisotropic (Halm and Dragon 1996), have been proposed and validated for concrete damage behavior. The bond-slip interaction between concrete and steel is addressed by incorporating specialized elements like contact or interface elements (Murcia-Delso and Benson Shing 2015; Casanova et al. 2012). Although this method achieves reliable accuracy, it demands substantial computational resources, particularly for large-scale structures such as RC bridges (Babazadeh et al. 2015).

Unlike the continuum method, frame elements, including lumped and distributed plasticity methods, are more attractive due to their reduced computational requirements. Among these, the fiber beam element is the most preferred for studying the seismic behavior of RC structures (Taucer et al. 1991; Spacone et al. 1996). In this approach, the section is discretized into multiple fibers, and uniaxial constitutive relations govern each fiber according to materials. Such a method allows for the independent modeling of the nonlinear behavior of concrete and steel. The longitudinal behavior is commonly integrated with the Euler–Bernoulli beam theory, where the shear deformations are neglected (Spacone et al. 1996). Then, the

¹Ph.D. Student, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy. Email: jiahui.shen@polito.it

²Assistant Researcher, Laboratório Nacional de Engenharia Civil, Lisboa 1700-066, Portugal. ORCID: <https://orcid.org/0000-0002-4140-2204>. Email: marruda@lnec.pt

³Full Professor, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy (corresponding author). ORCID: <https://orcid.org/0000-0001-9074-2558>. Email: alfonso.pagani@polito.it

⁴Full Professor, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy. Email: erasmo.carrera@polito.it

⁵Associate Professor, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy. Email: enrico.zappino@polito.it

⁶Assistant Professor, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy. Email: riccardo.augello@polito.it

⁷Associate Professor, *Mul 2 Lab*, Dept. of Mechanical and Aerospace Engineering, Politecnico di Torino, Torino 10129, Italy. Email: marco.petrolo@polito.it

Note. This manuscript was submitted on February 2, 2024; approved on January 31, 2025; published online on May 23, 2025. Discussion period open until October 23, 2025; separate discussions must be submitted for individual papers. This paper is part of the *Journal of Structural Engineering*, © ASCE, ISSN 0733-9445.

behavior of the entire RC member can be approximated by a limited number of beam elements through standard finite element (FE) approaches. Notably, it has been reported that a single force-based element can effectively simulate the nonlinear response of a frame member (Neuenhofer and Filippou 1997). Several approaches have been proposed to include the flexure–shear interaction in the beam–column elements, reviewed in Ceresa et al. (2007). The first way involves the introduction of shear springs at the end of the element, which is simple and easy for implementation but involves calibrating parameters (D’Ambrisi and Filippou 1999; Marini and Spacone 2006). The second method consists of integrating Timoshenko beam theory into the frame element and combined with multidimensional material constitutive laws, which ensure the capture of flexure–shear interaction at both material and section levels. Different Timoshenko fiber beam elements have been proposed so far, including displacement-based (Ceresa et al. 2009; Feng et al. 2017), force-based (Petrangeli et al. 1999; Mullapudi and Ayoub 2013), and mixed formulation-based (Saritas and Filippou 2009, 2013; Cheng and Shing 2022). However, classical Timoshenko beam elements often have difficulties accurately capturing nonlinear shear deformation due to the assumption of uniform shear stress or capturing localized phenomena (Urmson and Mander 2012; Girgin et al. 2018).

The tradeoff between accuracy and computational demands is challenging. A potential solution is represented by the higher-order beam theory based on Carrera Unified Formulation (CUF) (Carrera et al. 2014). Within the framework of CUF, 1D beam models are used to describe the 3D displacement field by using various cross-sectional expansion functions. This CUF-based beam theory provides a robust framework for overcoming limitations encountered in classical beam models without relying on additional assumptions. These Euler–Bernoulli and Timoshenko beam theories are considered particular cases by adjusting kinematics in the CUF framework (Carrera et al. 2011). Compared to the previously mentioned frame elements, a more accurate nonlinear shear effect can be taken into account by this CUF-based beam model. Importantly, it provides 3D results comparable to those of 3D solid elements while maintaining the efficiency of the 1D model, which makes it applicable to complex structures such as those owning discontinuities. This capability is typically beyond the reach of both lumped and distributed plasticity models. Moreover, 3D material constitutive laws are directly used for structural analysis rather than the requirement for the inelastic element parameters, such as bending moment–curvature relationships in the lumped plasticity model.

The application of CUF-based higher-order beam theories has shown success in static and dynamic analyses across various engineering structures (Carrera et al. 2022; Shen et al. 2022). The Component-Wise (CW) approach, a recent development of CUF, considers the exact geometry and material properties within the calculations. These models incorporating the CW approach, referred to as refined CW models, are particularly beneficial for analyzing composite structures such as RC structures (Carrera et al. 2022; Nagaraj and Maiaru 2023). In Shen et al. (2023a), the CW models demonstrated the capability to predict overall softening behavior in RC beams without stirrups and to capture flexural failure in RC beams with stirrups. However, some small beam elements, whose lengths are equal to the diameter of the stirrups, are periodically used to represent the stirrups’ actual geometry accurately. This exact representation of stirrups in RC structures demands increased beam element discretization, leading to a significant rise in degrees of freedom (DoFs) of refined CW models. Furthermore, when dealing with areas of high-stress gradients, there is an increase in computational expense due to the need for more refined models. In the past, refined models were used across entire domains

(Shen et al. 2023a), which is often unnecessary and leads to computational inefficiencies, mainly when local effects are confined to small regions.

A more effective strategy involves applying the refined models only in the required regions, whereas lower-order or classical models are used in less critical areas. The challenge of joining two different structural models with incompatible kinematics has been extensively explored, with numerous solutions detailed in Carrera et al. (2018). In the present study, a new Node-Dependent Kinematics (NDK) approach (Carrera and Zappino 2017) is introduced in the framework of CUF. This method allows the assignment of distinct kinematic assumptions to different nodes within a single 1D beam element, enhancing accuracy in targeted regions through refined kinematics. A transition element can connect the elements with different kinematics, ensuring displacement continuity via the inherent shape functions in the FE formulation. The advantage of this approach is that the calculation is still within the CUF framework, and no extra formulations are added, which is beneficial for computational efficiency. Furthermore, the notable scalability of this method can avoid further mesh refinement in FE models for global–local analysis (Carrera et al. 2019; Nagaraj et al. 2023). Although the NDK approach has been previously applied to RC structures (Augello et al. 2023), its use has been limited to linear analysis.

In this context, the current study aims to extend the NDK approach to the damage analysis of RC structures in the framework of the 1D-CUF model. This study uses validated material models, such as the modified Mazars damage model for concrete and von Mises plasticity for steel. These have demonstrated mesh-independent results in previous researches (Shen et al. 2023b, 2024). The scope of investigation in this work is not only limited to RC beams but also includes more complex engineering structures. To the authors’ knowledge, it is the first study to apply global–local strategies like the NDK approach to the nonlinear damage analysis of RC structures. By using the NDK approach, regions susceptible to critical damage are modeled with higher refinement. In comparison, the lower class is applied to the rest, thereby saving computational costs while ensuring a relatively high accuracy. Hence, the proposed approach shows considerable potential for real-world engineering applications due to its scalability and the optimal balance between accuracy and computational efficiency.

Unified Higher-Order Beam Models

In the framework of CUF (Carrera et al. 2014), the 3D displacement field of 1D beam models can be derived using the cross-sectional expansion functions. In this work, the axial direction of a 1D beam model is denoted by y , and x and z represent the coordinates in the cross-sectional plane. Hence, the 3D displacement field of a beam-like structure is expressed as follows:

$$\mathbf{u}(x, y, z) = F_\tau(x, z)\mathbf{u}_\tau(y), \quad \tau = 1, 2, \dots, M \quad (1)$$

where $F_\tau(x, z)$ is the cross-sectional expansion function, $\mathbf{u}_\tau(y)$ denotes the vector of unknown displacements along the beam axis, τ is a summation notation, and M signifies the number of terms in the expansion functions. The selection of a particular expansion characterizes the capabilities of a structural model. Various options for $F_\tau(x, z)$ are thoroughly discussed in Carrera et al. (2014). For the current analysis, both Taylor and Lagrange polynomial expansions are considered, and their details are provided in the subsequent sections.

Taylor Expansion Models

Taylor expansions (TE) use the Taylor-like polynomials, with base terms of the form $x^m z^n$, where m and n are positive integers. In general, kinematics based on TEs can be named TE n , in which n indicates the order of Taylor-like polynomials. For instance, a second-order TE model (TE2) exploits a parabolic expansion of the Taylor-like polynomials, and the corresponding expansion expansions F_τ are

$$\begin{aligned} F_1 &= 1, & F_2 &= x, & F_3 &= z, \\ F_4 &= x^2, & F_5 &= xz, & F_6 &= z^2 \end{aligned} \quad (2)$$

Then, the 3D displacement field of the second-order TE model can be explicitly expressed as

$$\begin{aligned} u_x(x, y, z) &= u_{x_1} + xu_{x_2} + zu_{x_3} + x^2u_{x_4} + xzu_{x_5} + z^2u_{x_6} \\ u_y(x, y, z) &= u_{y_1} + xu_{y_2} + zu_{y_3} + x^2u_{y_4} + xzu_{y_5} + z^2u_{y_6} \\ u_z(x, y, z) &= u_{z_1} + xu_{z_2} + zu_{z_3} + x^2u_{z_4} + xzu_{z_5} + z^2u_{z_6} \end{aligned} \quad (3)$$

where $u_{x_1} \dots u_{z_6}$ are unknown variables of the problem.

Lagrange Expansion Models

Another class utilizes the Lagrange polynomial as the expansion functions F_τ , named the ‘‘Lagrange expansion (LE) model.’’ Within these models, the cross section can be divided into subdomains, which are connected with Lagrange points (LPs). The Lagrange polynomials are usually given in terms of normalized coordinates, and any arbitrary cross-sectional geometry can be described with the help of isoparametric formulation. The simplest quadrilateral Lagrange polynomial is the four-point (L4) set, and the corresponding functions are

$$F_\tau = \frac{1}{4}(1 + rr_\tau)(1 + ss_\tau), \quad \tau = 1, 2, 3, 4 \quad (4)$$

where r and s are the normalized coordinates in the natural reference system, and (r_τ, s_τ) are the coordinates of point τ .

Therefore, the 3D displacement of the LE model with four-point Lagrange polynomials can be given as

$$\begin{aligned} u_x(x, y, z) &= F_1u_{x_1} + F_2u_{x_2} + F_3u_{x_3} + F_4u_{x_4} \\ u_y(x, y, z) &= F_1u_{y_1} + F_2u_{y_2} + F_3u_{y_3} + F_4u_{y_4} \\ u_z(x, y, z) &= F_1u_{z_1} + F_2u_{z_2} + F_3u_{z_3} + F_4u_{z_4} \end{aligned} \quad (5)$$

where $u_{x_1} \dots u_{z_4}$ are unknown variables that are physical translational displacements of each LP.

Eq. (5) results from the interpolation of the displacements derived at LPs. Moreover, in practical applications, one can select from quadratic Lagrange polynomials incorporating 9 points (L9) or cubic LEs with 16 points (L16). The physical translational displacements at the LPs within the cross section correspond to the model’s DoFs. Therefore, higher-order Lagrange polynomials provide enhanced accuracy by offering a more significant number of DoFs through additional LPs.

Finite-Element Approach

The finite element method (FEM) is used to solve for axial displacement vectors as described in Eq. (1). Accordingly, the displacement field can be rewritten as

$$\mathbf{u}(x, y, z) = F_\tau(x, z)N_i(y)\mathbf{u}_{\tau i}, \quad i = 1, \dots, N_{NE} \quad (6)$$

where N_i denotes the shape function associated with beam node i , $\mathbf{u}_{\tau i}$ is the nodal displacement vector, and N_{NE} represents the number of nodes within each beam element. Similarly, the virtual variation of the displacement can be expressed as

$$\delta \mathbf{u}(x, y, z) = \delta \mathbf{u}_{sj} F_s(x, z) N_j(y), \quad j = 1, \dots, N_{NE} \quad (7)$$

The detailed information on beam shape functions can be found in Carrera et al. (2014). Commonly adopted beam elements include two-node linear (B2), three-node quadratic (B3), and four-node cubic (B4) configurations. Notably, the selection of beam elements is independent of the choice of expansion functions, which is a significant flexibility for 1D CUF models.

The 3D strain field, $\boldsymbol{\varepsilon} = \{\varepsilon_{xx}, \varepsilon_{yy}, \varepsilon_{zz}, \varepsilon_{xy}, \varepsilon_{xz}, \varepsilon_{yz}\}^T$, can be obtained through the strain–displacement relation, which can be expressed in a vectorial notation

$$\boldsymbol{\varepsilon} = \mathbf{B} \mathbf{u} \quad (8)$$

where $\mathbf{B}$ is the linear differential operator with two contributions:

$$\mathbf{B} = \mathbf{B}_\Omega + \mathbf{B}_y = \begin{bmatrix} \frac{\partial}{\partial x} & 0 & 0 \\ 0 & 0 & 0 \\ 0 & 0 & \frac{\partial}{\partial z} \\ 0 & \frac{\partial}{\partial x} & 0 \\ \frac{\partial}{\partial z} & 0 & \frac{\partial}{\partial x} \\ 0 & \frac{\partial}{\partial z} & 0 \end{bmatrix} + \begin{bmatrix} 0 & 0 & 0 \\ 0 & \frac{\partial}{\partial y} & 0 \\ 0 & 0 & 0 \\ \frac{\partial}{\partial y} & 0 & 0 \\ 0 & 0 & 0 \\ 0 & 0 & \frac{\partial}{\partial y} \end{bmatrix} \quad (9)$$

The 3D stress field, $\boldsymbol{\sigma} = \{\sigma_{xx}, \sigma_{yy}, \sigma_{zz}, \sigma_{xy}, \sigma_{xz}, \sigma_{yz}\}^T$, can be calculated through the constitutive relation, which is expressed as

$$\boldsymbol{\sigma} = \mathbf{C}_d \boldsymbol{\varepsilon} \quad (10)$$

where $\mathbf{C}_d$ is a 6×6 represents the 6×6 stiffness matrix of the damaged material. This study addresses material nonlinearities resulting from damage, requiring a Newton–Raphson scheme. The secant stiffness matrix is used in the incremental process for its simpler implementation than the tangent stiffness matrix, although this may result in slower convergence. More details on the damage model will be subsequently introduced.

Component-Wise Approach

Due to the previously mentioned physical meaning of Lagrange polynomials, the CW approach, an extension of 1D-CUF models, has been developed to accurately represent composite structures made of diverse materials (Nagaraj et al. 2022; Kaleel et al. 2018). This approach is also effective for RC structures made of steel and concrete. As depicted in Fig. 1, the cross section of such structure is discretized into multiple elements according to the material. Here, steel is denoted by the gray elements, while concrete is indicated in white. LPs are assigned at their boundaries to maintain displacement continuity at the interfaces of steel and concrete components. The behavior of RC structures is then modeled with the LEs over the discretized beam elements. This CW approach allows for the independent and simultaneous consideration of actual material and geometric properties of each component, leading to a more accurate representation of the structural behavior.

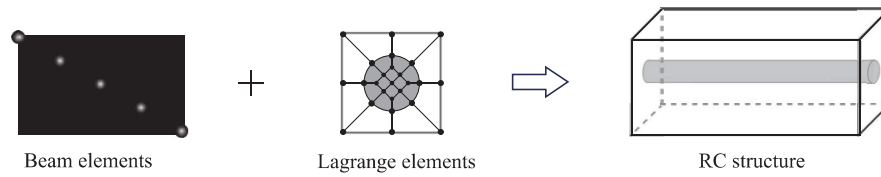


Fig. 1. An illustration of the beam model with CW approach for modeling RC structures.

Node-Dependent Kinematics Approach

As aforementioned, the 3D displacement field of beam elements is first approximated by the cross-sectional expansion $F_\tau(x, z)$ at node i , which is subsequently interpolated along the beam axis using the FE shape functions $N_i(y)$. Typically, uniform cross-sectional expansions are applied across all FE beam nodes. Classical beam theories can be realized in the framework of CUF by designing appropriate cross-sectional expansion. The aforementioned advanced TEs and LEs can overcome some limitations of these classical theories, particularly in complex scenarios, albeit at an increased computational cost.

In most cases, refined or higher-order models are only required in critical regions of the structure, such as areas with constraints or loadings and zones with concentrated stresses. In contrast, classical or lower-order models are sufficient for the rest of the noncritical regions. This strategy can reduce computational costs under the premise of high accuracy. For the connection between noncritical and critical zones, a node-dependent kinematics approach is proposed for transition. The NDK approach was first introduced in Carrera and Zappino (2017) and has since found widespread uses such as in Nagaraj et al. (2023) and Scano et al. (2023).

Beam Element with Node-Dependent Kinematics

An example of a beam structure is illustrated in Fig. 2, where the critical and noncritical regions are denoted by gray and white, respectively. In the NDK framework, the cross-sectional mechanical description $F_\tau(x, z)$ on each node is not uniform anymore, and it is further related to the node i , leading to node-dependent cross-sectional kinematics $F_\tau^i(x, z)$. Consequently, the number of terms in the expansion, M , differs at each node and is replaced with the notation M^i . The displacement fields are smeared through the same FE beam shape functions to ensure displacement continuity across

all points. The displacement representation for NDK beam elements, therefore, adopts the following form:

$$\mathbf{u}(x, y, z) = F_\tau^i(x, z)N_i(y)\mathbf{u}_{\tau i}, \quad i = 1, \dots, N_{NE};$$

$$\tau = 1, \dots, M^i \quad (11)$$

Besides, the variation of the corresponding displacement can be written

$$\delta\mathbf{u}(x, y, z) = \delta\mathbf{u}_{sj}F_s^j(x, z)N_j(y), \quad j = 1, \dots, N_{NE};$$

$$s = 1, \dots, M^j \quad (12)$$

Fig. 2 selects a two-node beam element within the transition zone for demonstration. Assuming the left node, marked in white, adopts a first-order TE while the right node, depicted in black, utilizes a linear LE with four nodes, the displacement field of Eq. (11) can be expressed as

$$\mathbf{u}(x, y, z) = N_1(y)[\mathbf{u}_{11} + \mathbf{u}_{21}x + \mathbf{u}_{31}z]$$

$$+ N_2(y)[\mathbf{u}_{12}L_1 + \mathbf{u}_{22}L_2 + \mathbf{u}_{32}L_3 + \mathbf{u}_{42}L_4] \quad (13)$$

where $L_1 \dots L_4$ are the Lagrange expression from Eq. (4).

FE Governing Equations

The governing equation for static problems is derived from the principle of virtual displacements, which states the equality of the external virtual work (δL_{ext}) and internal virtual work (δL_{int}). For simplicity, they are expressed as

$$\delta L_{int} = \int_V \delta \boldsymbol{\epsilon}^T \boldsymbol{\sigma} dV = \delta \mathbf{u}_{sj}^T \mathbf{K}^{\tau sij} \mathbf{u}_{\tau i} \quad (14)$$

$$\delta L_{ext} = \int_V \delta \mathbf{u}^T \mathbf{F} dV = \delta \mathbf{u}_{sj}^T \int_V N_j F_s^j \mathbf{F} dV = \delta \mathbf{u}_{sj}^T \mathbf{F}_{sj} \quad (15)$$

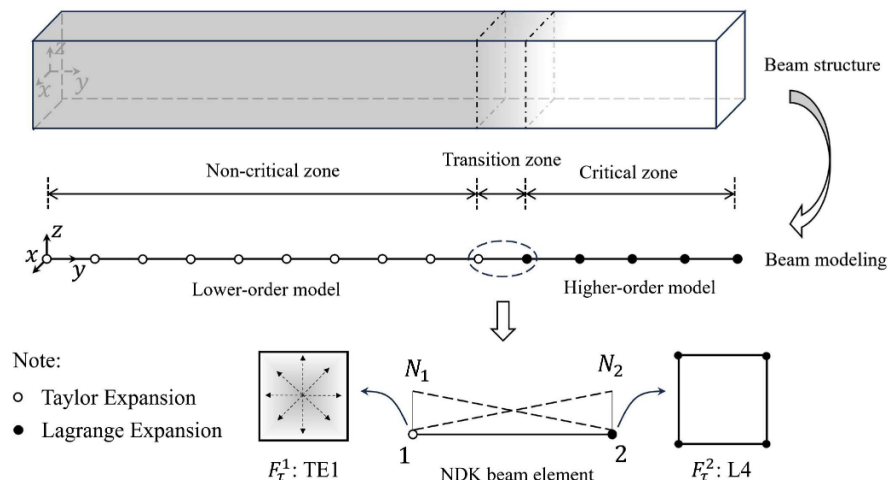


Fig. 2. A CUF-based 1D model with NDK approach.

with

$$\mathbf{K}^{\tau sij} = \int_l \int_{\Omega} [\mathbf{B}^T(N_j(y)F_s^j(x, z))\mathbf{C}_d\mathbf{B}(F_{\tau}^i(x, z)N_i(y))]d\Omega dl \quad (16)$$

where $\mathbf{K}^{\tau sij}$ is the fundamental nucleus in the form of the 3×3 stiffness matrix; l and Ω represent the length of beam element and area of cross section, respectively; i, j , and τ, s are indexes related to beam shape function and cross-sectional expansion function, respectively; $\mathbf{F}$ is the external load; and $\mathbf{F}_{sj}$ is the load vector in a 3×1 array. Thus, the governing equation can be expressed as

$$\mathbf{K}^{\tau sij}\mathbf{u}_{\tau i} = \mathbf{F}_{sj} \quad (17)$$

The matrix $\mathbf{K}^{\tau sij}$ is the basic block from which the stiffness matrix of the whole structure can be constructed automatically. It can be expressed as

$$\mathbf{K}^{\tau sij} = \begin{bmatrix} k_{xx}^{\tau sij} & k_{xy}^{\tau sij} & k_{xz}^{\tau sij} \\ k_{yx}^{\tau sij} & k_{yy}^{\tau sij} & k_{yz}^{\tau sij} \\ k_{zx}^{\tau sij} & k_{zy}^{\tau sij} & k_{zz}^{\tau sij} \end{bmatrix} \quad (18)$$

Extended forms for each component in Eq. (18) are detailed in Carrera and Zappino (2017). For brevity, the explicit expression of the first component $k_{xx}^{\tau sij}$, for an undamaged isotropic material, is given as follows:

$$\begin{aligned} k_{xx}^{\tau sij} &= C_{22} \int_{\Omega} F_{\tau, x}^i F_{s, x}^j d\Omega \int_l N_i N_j dy \\ &+ C_{66} \int_{\Omega} F_{\tau, z}^i F_{s, z}^j d\Omega \int_l N_i N_j dy \\ &+ C_{44} \int_{\Omega} F_{\tau}^i F_s^j d\Omega \int_l N_{i, y} N_{j, y} dy \end{aligned} \quad (19)$$

where C_{22} , C_{44} , and C_{66} are components of the material stiffness matrix, typically determined by the material's modulus of elasticity and Poisson's ratio.

Modified Mazars Damage Models

In this section, the isotropic concrete damage model proposed by Mazars (1984) is presented to capture the damage behavior of concrete. The model is modified with the fracture energy regularization technique to alleviate the mesh dependence based on the tensile and compressive constitutive laws (Arruda et al. 2022). The modified Mazars damage model does not consider permanent strains compared to other models. However, it is adequate for the damage analysis of RC structures subjected to quasi-static loads due to the role of steel reinforcement in governing the plastic behavior of such structures. To this end, the von Mises yield criterion is used to describe the plasticity of steel reinforcements.

According to Mazars (1984), the evolution of isotropic material stiffness is directly controlled by one scalar damage variable d , which ranges from 0 to 1.0. The formulation of the original Mazars damage model is given as follows:

$$\boldsymbol{\sigma} = \mathbf{C}_d \boldsymbol{\varepsilon} = (1 - d)\mathbf{C}\boldsymbol{\varepsilon} \quad (20)$$

where $\mathbf{C}$ represents the material stiffness matrix without damage.

In the Mazars damage model, damage initiation and evolution are governed exclusively by positive strains in the principal directions. Therefore, Mazars introduced an equivalent strain, denoted

as $\boldsymbol{\varepsilon}_{eq}$, to cover this behavior. This equivalent strain is calculated according to the following expression:

$$\boldsymbol{\varepsilon}_{eq}(\boldsymbol{\varepsilon}) = \sqrt{\sum_{i=1}^3 \langle \varepsilon_i \rangle_+^2} \quad (21)$$

in which $\langle \cdot \rangle_+$ is the Macauley bracket for picking out the positive value, and ε_i are the principle strains.

Subsequently, the loading function, denoted as $f(\boldsymbol{\varepsilon}, \kappa) = \boldsymbol{\varepsilon}_{eq}(\boldsymbol{\varepsilon}) - \kappa$, depends on the equivalent strain and a damage threshold κ . Before damage occurrence, κ is a material constant that equals the maximum elastic strain. After damage initiation, it is updated to the current value of $\boldsymbol{\varepsilon}_{eq}$. If $f(\boldsymbol{\varepsilon}, \kappa) = 0$ occurs, it indicates the onset of damage, requiring an update to the damage variable. This update is governed by a linear combination of tensile and compressive damage variables, d_t and d_c , and the formulation is expressed as:

$$d = \alpha_t d_t + \alpha_c d_c \quad (22)$$

where α_t and α_c are weights factors for the tensile and compressive damage variables, d_t and compression d_c , respectively. The explicit calculation of α_t and α_c can be found in Arruda et al. (2022).

Rather than using original damage propagation laws for d_t and d_c from Mazars (1984), this work adopts modified damage evolution laws based on concrete stress-strain relations from fib Model Code 2010 (MC2010) (fib Special Activity Group 2013), which are more practical. In addition, a fracture energy regularization technique based on the crack band model is used to regularize the softening behavior and address the mesh dependency issues.

For tensile responses, the bilinear softening constitutive law from MC2010 may lead to numerical convergence issues when the stress diminishes to zero and the damage ascends to one. To circumvent this, a classical constitutive law with an exponential softening curve is used. The explicit formulation of tensile damage evolution is derived and expressed as:

$$d_t = g_t(\kappa_t) = 1 - \frac{\varepsilon_{d0}}{\kappa_t} \exp\left(\frac{\varepsilon_{d0} - \kappa_t}{\varepsilon_{tu} - \varepsilon_{d0}}\right) \quad (23)$$

where ε_{d0} is the elastic strain limit corresponding to the peak stress, also known as the mean uniaxial tensile strength f_{cm} ; and ε_{tu} signifies the equivalent ultimate strain for bilinear softening and is associated with the volumetric fracture energy g_{ft} and crack bandwidth l_c .

Similarly, the damage evolution law for compression is derived from the compressive stress-strain relationship, which can be expressed as follows:

$$d_c = g_c(\kappa_c) = \begin{cases} 1 - \frac{(k \times \eta - \eta^2)f_{cm}}{(1 + (k - 2) \times \eta)E_{cm}\kappa_c} & \text{if } \kappa_c \leq \varepsilon_{c1} \\ 1 - \frac{f_{cm}}{E_{cm}\kappa_c} & \text{if } \varepsilon_{c1} < \kappa_c \leq \varepsilon_{c2} \\ 1 + \frac{k_1}{E_{cm}} - \frac{k_2}{E_{cm}\kappa_c} & \text{if } \varepsilon_{c2} < \kappa_c \leq \varepsilon_{cres} \\ 1 - \frac{\sigma_{cres}}{E_{cm}\kappa_c} & \text{if } \varepsilon_{cres} < \kappa_c \end{cases} \quad (24)$$

with

$$\kappa_c = \frac{\kappa_t}{\nu\sqrt{2}}; \quad \eta = \frac{\kappa_c}{\varepsilon_{c1}}; \quad k = \frac{1.05E_{cm}\varepsilon_{c1}}{f_{cm}};$$

$$k_1 = \frac{f_{cm}}{(\varepsilon_{cu} - \varepsilon_{c2})}; \quad k_2 = f_{cm} + k_1 \times \varepsilon_{c2}$$

where f_{cm} is the mean compressive strength of the concrete; E_{cm} denotes the secant Young's modulus; k , k_1 , and k_2 are parameters from CEN (2005) to describe the softening part of constitutive laws; ε_{c1} and ε_{c2} are strain parameters adopted from CEN (2005); η is a unidimensional strain ratio provided in fib Special Activity Group (2013); σ_{res} is residual compressive stress that ensures stress never reaches 0.0 to avoid convergence issues; ε_{res} is the corresponding residual compressive strain; and ε_{cu} is the equivalent ultimate compressive strain when neglecting the residual stress, and is associated with the compressive volumetric fracture energy g_{fc} and crack bandwidth l_c .

One key issue in fracture energy regularization is determining the correct value of l_c for obtaining objective numerical results. It is recognized that various factors, including element shape, element order, and element size, can influence the value of l_c . In this work, the estimation method of l_c from Shen et al. (2024) has been adopted. More details of this method can be explored in Shen et al. (2024).

Numerical Examples

This section presents four illustrative examples of RC structures selected from existing literature to demonstrate the proposed approach's numerical performance. The first three examples focus

on RC beams, while the last one involves an RC frame. All numerical simulations are conducted using a displacement control method.

Notched Reinforced Concrete Beam under Tension

The first example is a direct tension test on a notched RC beam, which was conducted experimentally in Ouyang et al. (1997). Although the CUF-CW solution has been previously applied to this case (Nagaraj and Maiaru 2023), further investigation is now placed on NDK models using this simple example. The concrete beam is reinforced with three evenly spaced longitudinal bars. Two notches, each 10 mm deep and 12.7 mm wide, are prefabricated in the middle to initiate the first crack. Fig. 3 depicts the overall load layout and geometries. The left end is fixed in all directions, while a displacement-controlled pressure is applied to the right end. The material properties are adopted from Nagaraj and Maiaru (2023) and listed in Table 1.

Beam element discretization is conducted along the longitudinal axis of the structure, with Fig. 4(a) illustrating that black dots stand for the nodes of beam elements. More beam elements are assigned around the middle notches as suggested from Nagaraj and Maiaru (2023). This refinement may be critical for accurately capturing the stress concentration and subsequent damage initiation. Cross-sectional discretizations are visualized in Fig. 4(b), where circles represent the steel component within the beam. The steel is integrated into the concrete matrix using LPs so that displacement continuity can be satisfied, which is also the strategy of the CW approach.

In Nagaraj and Maiaru (2023), only five and seven quadratic beam elements with quadratic Lagrange elements were used. Although these models presented satisfactory correlations with experimental load–displacement curves, the limited number of beam

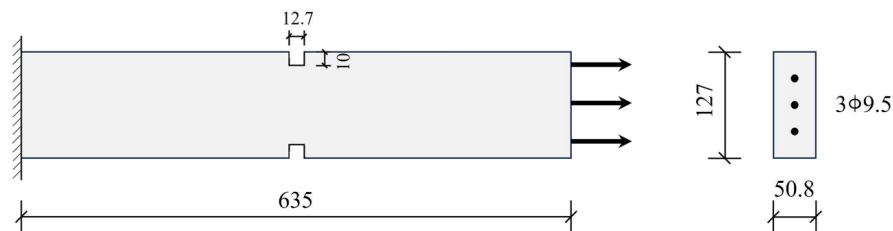


Fig. 3. Load layout and geometry of notched RC beams under direct tension (unit: mm).

Table 1. Material properties of the notched RC beams

Material type	E (GPa)	f_{ctm} (MPa)	f_{cm} (MPa)	G_{ft} (N/m)	G_{fc} (N/m)	ν	f_y (MPa)
Concrete	27.349	3.19	44	144	22,150	0.175	—
Steel	191.584	—	—	—	—	0.28	508

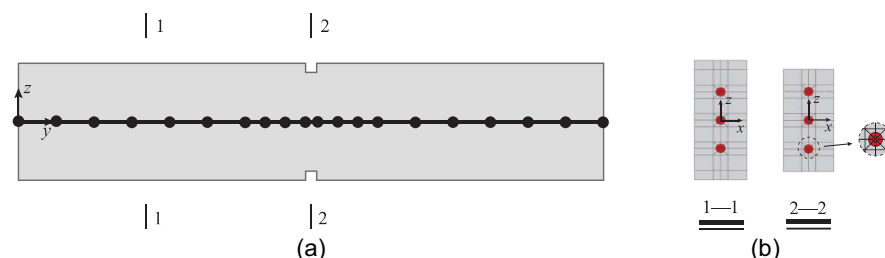


Fig. 4. (a) FE discretization of beam elements; and (b) cross-sectional discretization for the notched RC beam.

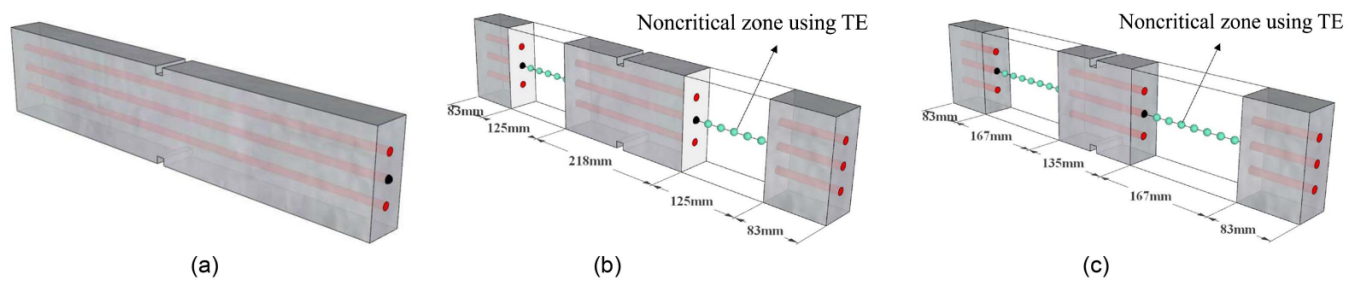


Fig. 5. Different models adopted for the analysis of the notched RC beam: (a) refined CW model; (b) NDK1 model; and (c) NDK2 model.

Table 2. Model information of the notched RC beams

Model number	Model 1	Model 2	Model 3	Model 4	Model 5	Model 6	Model 7
Model type	Refined	NDK1	NDK1	NDK1	NDK2	NDK2	NDK2
TE order	—	TE1	TE2	TE3	TE1	TE2	TE3
DoFs	43,677	31,257	31,347	31,467	26,289	26,415	26,583

elements constrained the prediction of accurate damage distribution. The current analysis uses a finer mesh with 17 quadratic beam elements coupled with the same quadratic Lagrange elements for cross-sectional expansion. The beam model in which all nodes are expanded via LEs is named the “refined CW model,” as depicted in Fig. 5(a). This model can enhance the numerical accuracy, but the required DoFs are relatively high. For the investigation of the NDK approach, two models are presented in Figs. 5(b and c). Notably, both NDK models adopt an identical mesh discretization to the refined CW model. The difference lies in the expansion functions assigned to specific beam nodes as needed. For instance, TEs are assigned to beam nodes in noncritical zones, identified as white regions in Figs. 5(b and c), and LEs are used for the remaining nodes. Compared to the NDK1 model, the NDK2 model tries to increase the number of beam nodes using TEs, further reducing computational expenses. Moreover, the influence of TE order on the structural analysis is also investigated in this part. All information of different models is listed in Table 2.

Fig. 6 presents the load–deflection responses of the notched RC beam according to the aforementioned models, alongside

the corresponding experimental results for comparison. The curve of Model 1 agrees well with the experimental data, demonstrating the strong capability of the CW approach in addressing this type of composite structure. Therefore, Model 1 should be regarded as a refined CW model whose performance can be considered a benchmark for NDK models.

When the NDK approach is applied, as illustrated in Fig. 6, all NDK models initially exhibit linear behavior identical to that of Model 1. Upon the onset of damage, all NDK models present a consistent structural response. However, the hardening curves of all NDK models are marginally higher than those observed in the experimental data and simulated by Model 1. This slight discrepancy may be attributed to the reduced DoFs in some beam areas. Comparison between Figs. 6(a and b) reveals that the NDK2 model predicts marginally steeper hardening curves, suggesting that the reduction in DoFs has a slight impact on the structural response during hardening.

To better understand the previously described discrepancy, Fig. 7 presents the final damage distribution for each model. According to Fig. 7(a), the expected pattern is observed. The entire beam exhibits

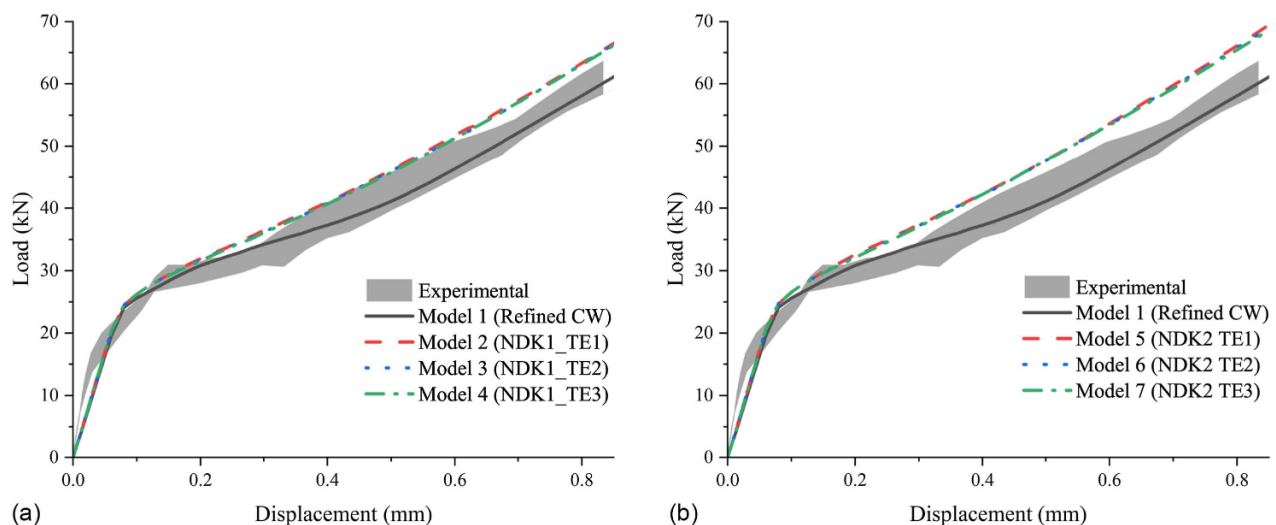


Fig. 6. Load–deflection curves from experimental test, refined CW model: (a) NDK1 models; and (b) NDK2 models for the notched RC beam.

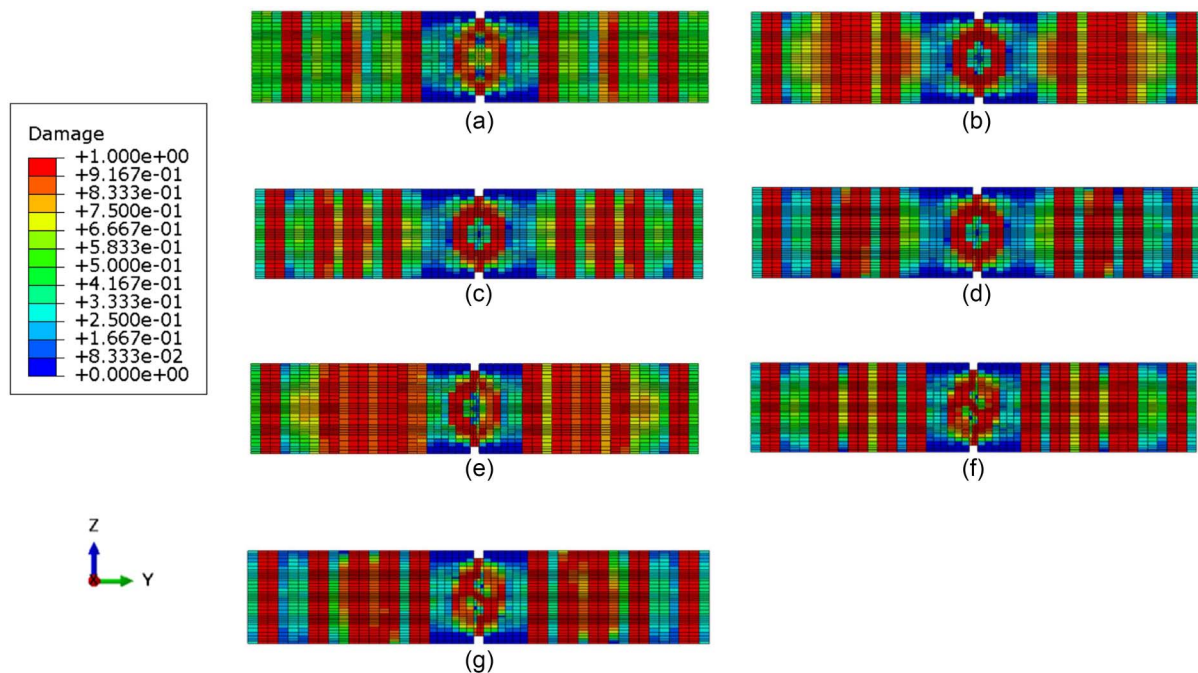


Fig. 7. Final damage distributions of the notched RC beam from: (a) Model 1 (refined CW); (b) Model 2 (NDK1 TE1); (c) Model 3 (NDK1 TE2); (d) Model 4 (NDK1 TE3); (e) Model 5 (NDK2 TE1); (f) Model 6 (NDK2 TE2); and (g) Model 7 (NDK2 TE3).

damage to varying degrees, with a fully damaged zone appearing distinctly and periodically along the beam. The concrete between these zones shows signs of unloading, indicating strain increments are localized in some narrow bands while the rest undergo unloading.

In contrast, Fig. 7(b) indicates that areas using linear TE are depicted as fully damaged, which may not be reasonable. Applying second-order and third-order TEs to the same areas results in a recurrence of the distributed damage zones, as shown in Figs. 7(c and d), but they are denser than those in Fig. 7(a). This phenomenon is also observable from Figs. 7(e–g).

Therefore, it can be inferred that the NDK models tend to overestimate damage compared to the refined CW model due to the limited DoFs, which further leads to a relatively higher hardening structural behavior. The NDK2 models amplify this phenomenon compared to the NDK1 models due to the increased number of beam elements using TE, which can account for the slightly higher hardening curves observed in Fig. 7(b) relative to those from NDK1 models in Fig. 7(a). Nonetheless, the divergence between the results from NDK models and experimental data or refined CW model is considered acceptable given the computational efficiency benefits. Specifically, the NDK2 model demonstrates an approximate 40% reduction in DoFs compared to the refined CW model,

rendering them preferable to the NDK1 model, which offers about a 28.4% reduction in DoFs.

Four-Point Bending Reinforced Concrete Beam

RC beams under a four-point bending test are commonly seen in experimental campaigns because they reflect typical working conditions of RC beams. A benchmark experiment, as reported in Firmo et al. (2018), was simulated using a CUF-based higher-order beam model detailed in Shen et al. (2023a). Although this model in Shen et al. (2023a) produced mesh-independent results, it still required a relatively large number of DoFs. Therefore, this study reviews the same benchmark. Fig. 8 shows the load layout and geometric details. The concrete beam is reinforced with stirrups every 60 mm throughout the length. A displacement control method with a maximum value of 25 mm is used for numerical simulations. The material properties are listed in Table 3.

A half-structure model, as depicted in Fig. 9, was utilized for numerical simulation owing to the symmetry. The nodes on the midspan symmetry plane were restrained against displacement along the axial coordinate. Fig. 9(a) illustrates the discretization of beam elements, with black dots representing nodes of beam elements. It should be noted that the node positions and quantities

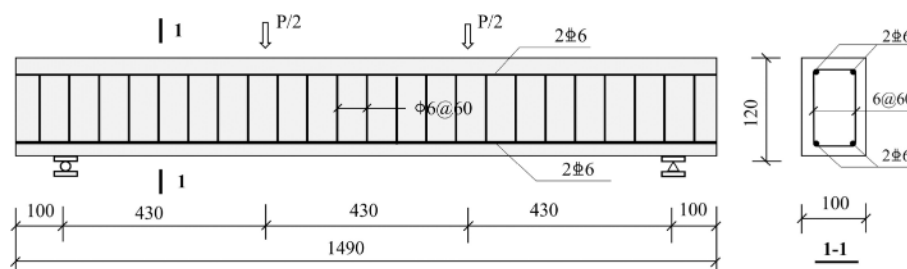
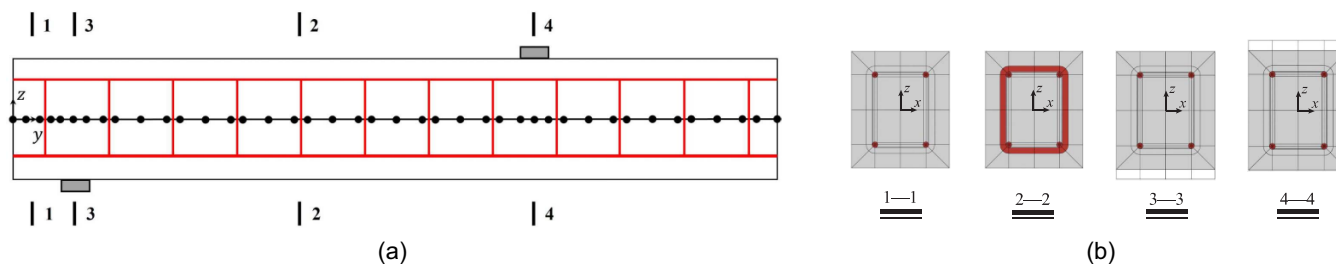


Fig. 8. Load layout and geometry of RC beams under four-point bending (unit: mm).

Table 3. Material properties of the four-point bending RC beam

Material	E (GPa)	f_{ctm} (MPa)	f_{cm} (MPa)	G_f (N/m)	G_{fc} (N/m)	ν	f_y (MPa)	f_{yu} (MPa)
Concrete	31.0	2.8	37	140.0	21,000	0.2	—	—
Steel	193	—	—	—	—	0.3	546	691

**Fig. 9.** (a) FE discretization of beam elements; and (b) cross-sectional discretization for the four-point bending RC beam.

are only for illustration rather than for actual numerical calculation. Fig. 9(b) presents four cross-sectional discretizations, with white areas representing the elastic plates for loading and support and the gray regions denoting concrete components. Nodes at the steel–concrete interface are shared to ensure displacement continuity between steel and concrete components.

To evaluate the efficiency of the NDK solution, Table 4 lists six models where Model 1 and Model 5 use LEs for all beam nodes, and the rest adopts the NDK approach. Model 1 and Model 5 are acknowledged as refined CW solutions because their accuracies have been confirmed in Shen et al. (2023a).

Based on the refined CW model, three different NDK models are introduced in Fig. 10. Since the midspan of bending RC beams is susceptible to damage and failure, NDK1 uses LEs in the midspan and support zones, while the remaining uses TE1. This strategy ensures detailed damage capture in the critical midspan region while optimizing computational resources elsewhere. For comparison, NDK2 and NDK3 apply a greedy approach in which only the supporting and loading parts are assigned with LEs and use TEs elsewhere to highlight the importance of midspan. It should be noted that all models adhere to the same cross-sectional discretizations as depicted in Fig. 9(b).

Fig. 11 plots the load–deflection response of various models, including the experimental curve for comparison. Initially, there is an excellent agreement between the experimental data and the numerical predictions across all models during the elastic phase. The variance between the numerical and experimental crack loads has been previously discussed in Shen et al. (2023a). After the elastic step, Models 3 and 4 start to diverge from the expected behavior, failing to simulate the structural response, particularly after steel yielding accurately. The reason can be found in Figs. 10(c and d), where both models exhibit unreasonable damage compared to Model 1. This inaccuracy results from the inability of TE to provide sufficient DoFs despite the significant reduction in computational demands provided by Models 3 and 4.

Consequently, while NDK2 and NDK3 models are applicable for the elastic range, they are too rough to model the correct hardening behavior.

When comparing the responses from Model 1 and Model 2, as depicted in Fig. 11, the load–deflection curve for the NDK1 model is marginally higher than that of the refined CW model. This variation can be attributed to the reduced DoFs caused by using TE in the shear regions in Model 2, resulting in a stiffer response. As illustrated in Fig. 12, the damage distribution of Model 2 in the shear area is akin to that of Models 3 and 4. However, the damage captured in the midspan of Model 2 is similar to that of Model 1. Both models capture vertical damage in the tensile zones and compressive damage at the top in the midspan, which agrees with the experimental crack distribution shown in Fig. 13. Hence, Model 2 can still accurately reflect the load–deflection response, highlighting the greater significance of the structural behavior at the midspan compared to the shear regions in this structure. A similar observation on load–displacement curves and damage distributions is noted when comparing Models 5 and 6, reinforcing the accuracy of the NDK1 model.

In addition, the von Mises stress distributions of concrete and steel for Models 5 and 6 at the final step are depicted in Figs. 14 and 15, respectively. The von Mises stress distributions in the middle span of both models are similar. The von Mises stresses of concrete in the tensile zones are nearly zero, resulting from tensile strain softening or unloading due to tensile damage. Meanwhile, the von Mises stresses in the compressive zones reach or approximate the compressive strength, indicating the occurrence of compressive damage. Furthermore, both models demonstrate that the von Mises stresses in the longitudinal rebars of the bottom layer reach yield stress, as illustrated in Fig. 15. A discrepancy in the stress within the shear zones between the two models can be attributed to the limited DoFs in the shear zones of the NDK models. However, this limitation does not affect the structural performance of the NDK1 model because the investigated RC

Table 4. Model information of the four-point bending RC beam

Model number	Model 1	Model 2	Model 3	Model 4	Model 5	Model 6
Model type	Refined CW	NDK1	NDK2	NDK3	Refined CW	NDK1
Beam elements	40B2	40B2	40B2	40B2	40B4	40B4
DoFs	55,551	19,263	4,491	4,848	163,743	59,163

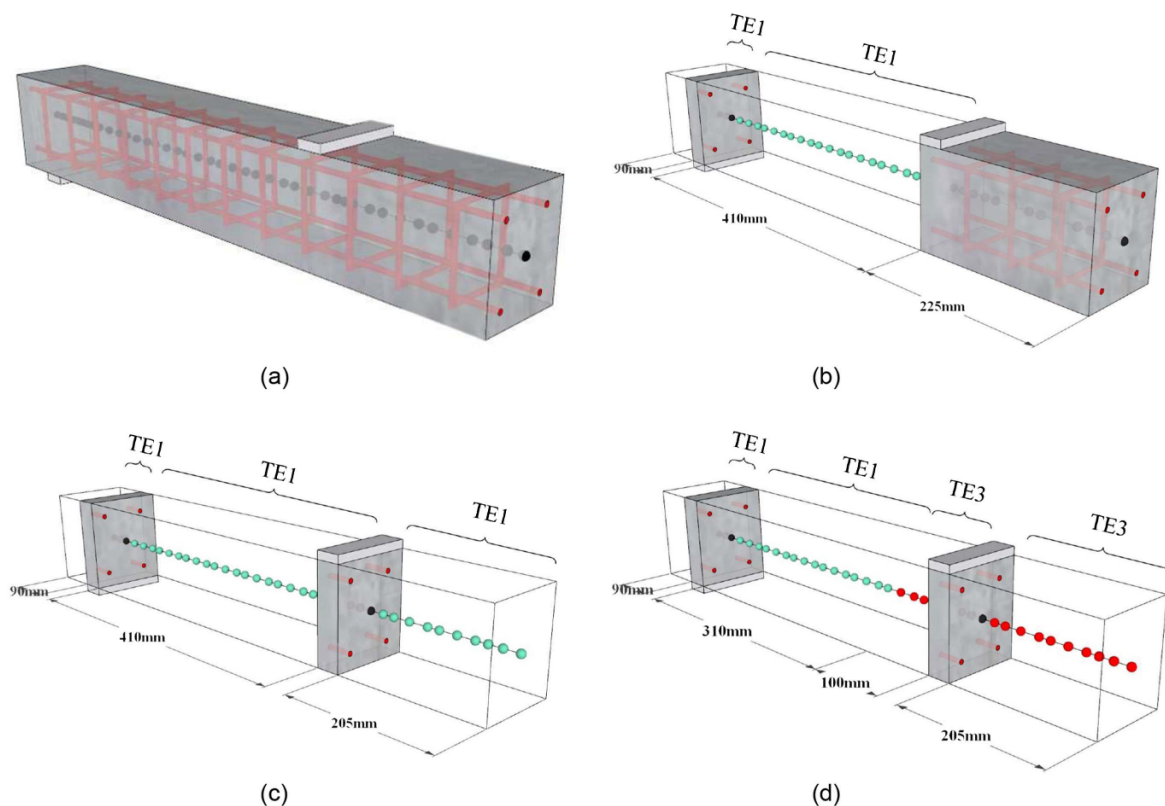


Fig. 10. Different models adopted for the analysis of the four-point bending RC beam: (a) refined CW model; (b) NDK1; (c) NDK2; and (d) NDK3.

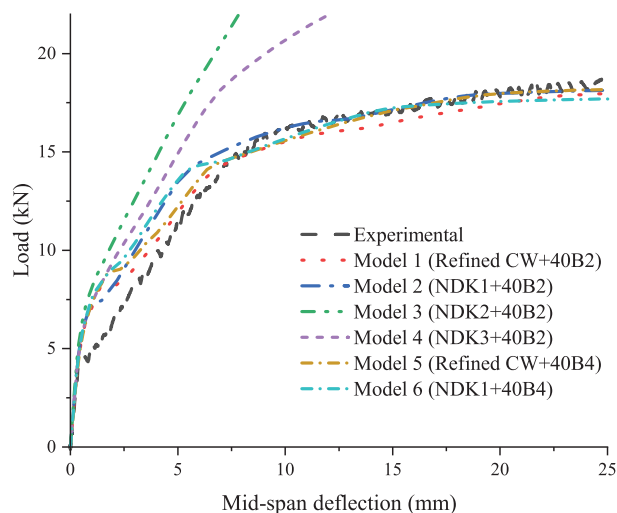


Fig. 11. Load-deflection curves for four-point bending RC beams.

beam is flexure-dominant, with the midspan being particularly critical and susceptible to damage. NDK1 model uses higher-order models for the midspan zone, ensuring its accuracy.

Regarding computational costs, Model 2 exhibits an approximately 65% reduction in DoFs compared to Model 1, while Model 6 offers a similar reduction relative to Model 5. These findings underscore the advantage of the NDK1 model in balancing computational efficiency with high fidelity in structural response simulation.

Reinforced Concrete Beam with Web Openings

RC beams with web openings are commonly implemented where passing ducts to accommodate vital utilities are necessary. These openings inevitably result in a decrease in stiffness and localized damage, weakening the overall structural performance. A detailed investigation of web openings and their surroundings is important. For this reason, an RC beam with web openings, ideal for applying the NDK approach, is examined as the third case study. A group of experimental campaigns for an RC beam with web opening was reported in Elsanadedy et al. (2019). One selected specimen from Elsanadedy et al. (2019) is illustrated in Fig. 16, where two rectangular web openings with 450×225 mm are created in the shear zone of the RC beam. The experiment was specifically designed to investigate the response of an RC beam after introducing post-construction openings without any additional strengthening methods. The rest of the experimental conditions are the same as those from the second case. According to Elsanadedy et al. (2019), the compressive strength of concrete was 50 MPa, measured from cube tests. A strength of 40 MPa is estimated from fib Special Activity Group (2013) to align this with cylinder test results. The concrete Young's modulus was unknown; however, preliminary numerical analysis were conducted to approximate the modulus by fitting the experimental linear response. As a result, the Young's modulus of concrete is estimated to be 24 GPa. Additional material properties are listed in Table 5.

Similarly, only half-structures are modeled for numerical analysis due to the benefit of symmetry. Fig. 17(a) illustrates the assignment of beam elements, with six distinct cross sections identified to accommodate stirrups, loading plates, and web openings. Fig. 17(b) depicts the respective cross-sectional discretizations.

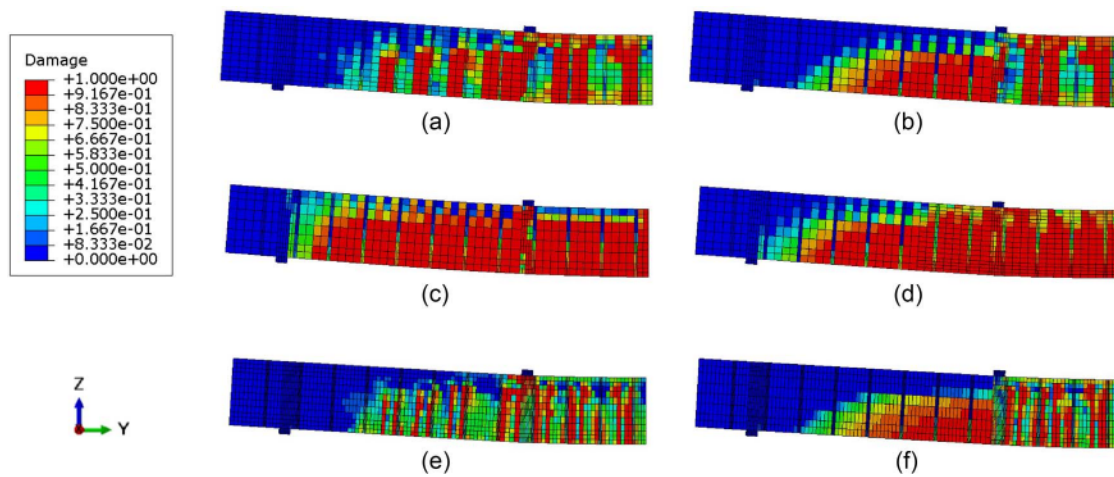


Fig. 12. Final damage distribution of four-point bending RC beams from: (a) Model 1 (refined CW + 40B2); (b) Model 2 (NDK1 + 40B2); (c) Model 3 (NDK2 + 40B2); (d) Model 4 (NDK3 + 40B2); (e) Model 5 (Refined CW + 40B4); and (f) Model 6 (NDK1 + 40B4).

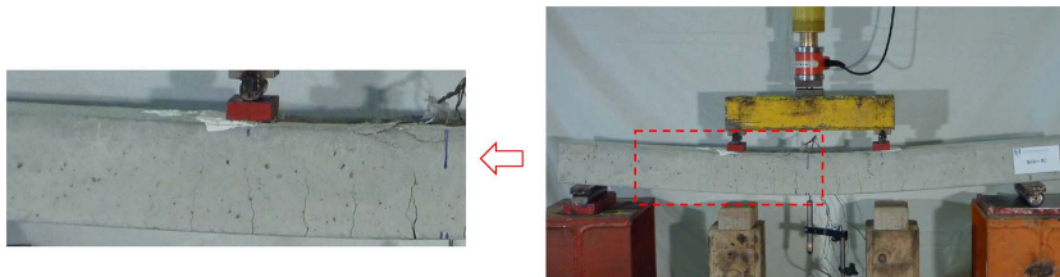


Fig. 13. Experimental cracks of four-point bending RC beam (Firmo 2015).

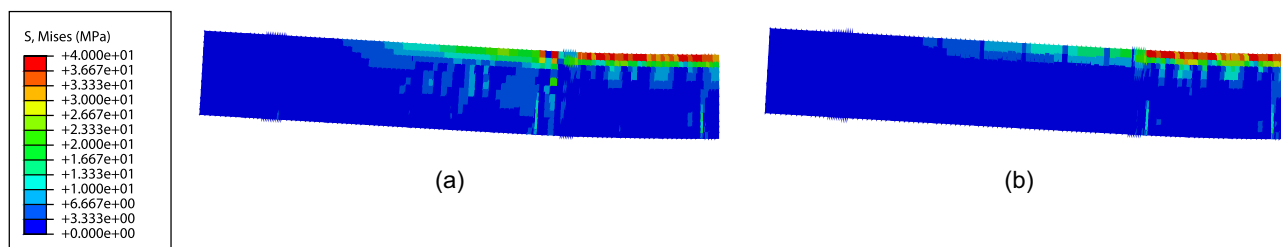


Fig. 14. Von Mises stress distribution of concrete in four-point bending RC beam from: (a) Model 5 (refined CW + 40B4); and (b) Model 6 (NDK1 + 40B4) at displacement of 25 mm.

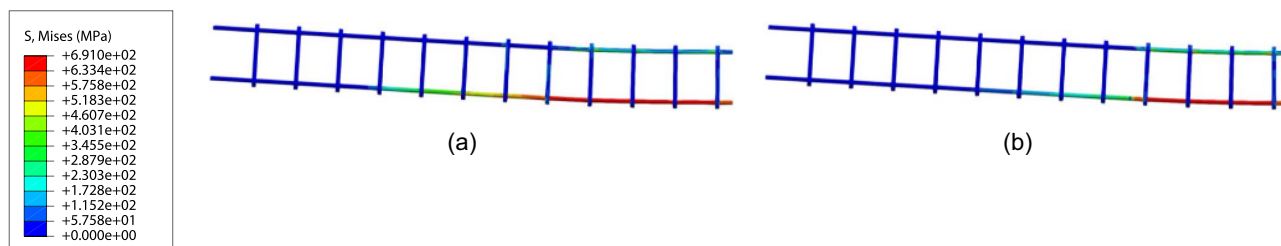


Fig. 15. Von Mises stress distribution of steel reinforcement in four-point bending RC beam from: (a) Model 5 (refined CW + 40B4); and (b) Model 6 (NDK1 + 40B4) at displacement of 25 mm.

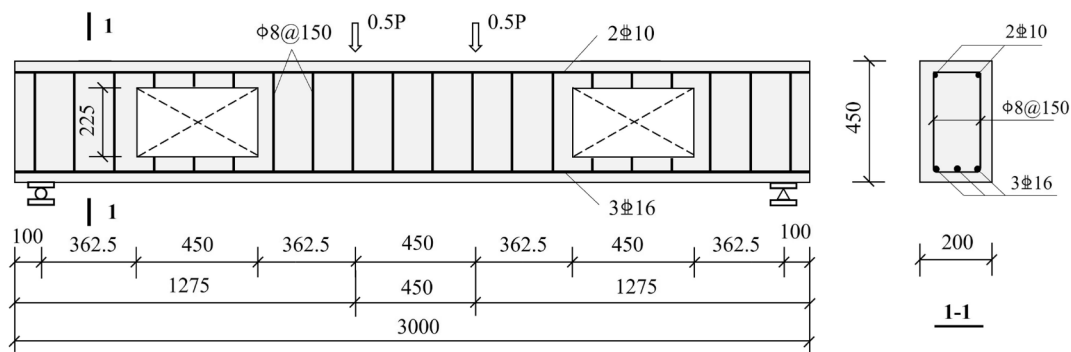


Fig. 16. Load layout and geometry of the RC beam with web openings (unit: mm).

Table 5. Material properties of the RC beam with web openings

Material	E (GPa)	f_{ctm} (MPa)	f_{cm} (MPa)	G_{ft} (N/m)	G_{fc} (N/m)	ν	f_y (MPa)
Concrete	24.0	2.3	40	70.0	21,627	0.2	—
Steel	200	—	—	—	—	0.3	575

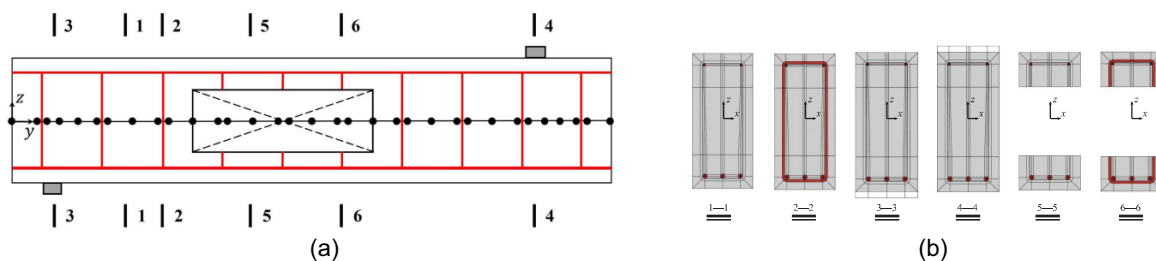


Fig. 17. (a) FE discretization of beam elements; and (b) cross-sectional discretization for the RC beam with web openings.

Four numerical models are designed for the damage analysis, and the corresponding model information is detailed in Table 6. All models use consistent cross-sectional discretizations and utilize L9 elements when implementing LEs. Model 1 and Model 2 adopt more beam elements than Model 3 and Model 4, ensuring sufficient DoFs for simulations. It is expected that most damage will manifest near the web openings, and some will occur at the bottom of the midspan. Then, one designed NDK model illustrated in Fig. 18(b) is applied to Models 2 and 4 to demonstrate the effectiveness of the NDK approach. From the previous two examples, the order of TE plays a less important role compared to the length of TE. Therefore, only linear TE is used where necessary in Models 2 and 4.

The load–midspan displacement curves are shown in Fig. 19, comparing numerical simulations and experimental data. Up to a displacement of 3 mm, numerical results closely agree with the experimental data, effectively capturing the linear behavior and initial damage stage. As displacement increases, numerical curves start to deviate from the experimental benchmark. Despite this divergence, the hardening parts of the numerical curves are still parallel to

the experimental hardening curves. The experimental curve then reaches the peak load and exhibits a sharp drop, whereas the numerical curves do not display a significant decrease. This discrepancy will be explained in the subsequent discussion.

When comparing Model 1 to Model 3, their curves coincide closely until reaching the peak load. The fluctuation in peak loads between these two models is likely due to the difference in the element approximation used, with cubic beam elements providing better precision over linear ones. A similar phenomenon is observed between Model 2 and Model 4. Variations in the results between refined CW models and NDK models are within acceptable ranges because of the utilization of lower-order TE at some beam element nodes, leading to slightly softer numerical models. Nevertheless, the NDK model achieves a significant reduction in the DoFs, approximately 35.3% for B2 elements and 36.6% for B4 elements.

The experimental campaign revealed shear failures in the top and bottom chords, as depicted in Fig. 20, which can explain the sharp drop in reaction load observed in the experimental results shown in Fig. 19. This phenomenon can be attributed to the use of U-shaped stirrups, which reduced bonding effectiveness and caused the concrete in the top and bottom chords to behave similarly to plain concrete, thereby leading to the pronounced diagonal shear cracks observed during the experiment.

However, the numerical damage patterns shown in Fig. 21 fail to replicate these distinct diagonal cracks, which further explains why the numerical models do not exhibit a similar drop in reaction load

Table 6. Model information of the RC beam with web openings

Model number	Model 1	Model 2	Model 3	Model 4
Model type	Refined CW	NDK	Refined CW	NDK
Beam order	79B2	79B2	42B4	42B4
DoFs	145,641	94,215	231,558	146,820

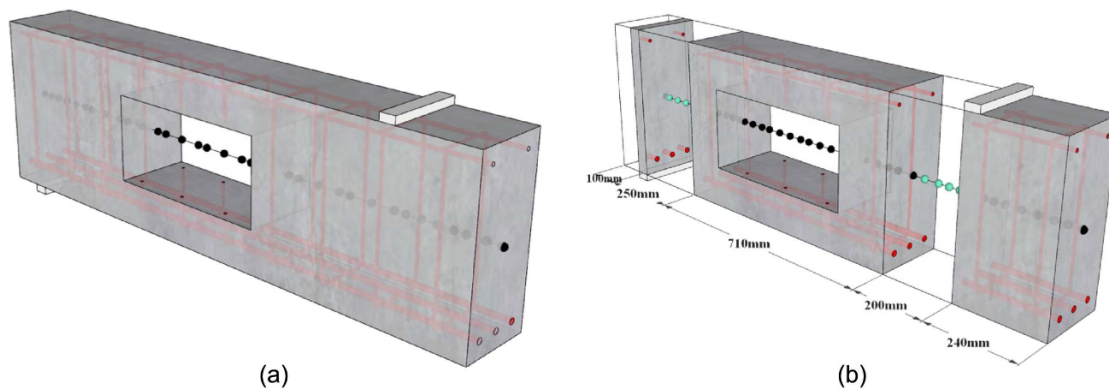


Fig. 18. (a) Refined CW model; and (b) NDK model for the analysis of the RC beam with web openings.

as observed in the experimental results in Fig. 19. There are two primary reasons for this discrepancy. First, the assumption of a perfect bond between rebars and surrounding concrete in the proposed numerical models allows the stirrups in the chords to continue resisting shear forces, resulting in vertical damage distributions in the opening zones. Second, the damage model used in this work only considers Mode 1 failure, making it difficult to capture Mode 2 shear failure accurately.

Although the experimental study detailed in Elsanadedy et al. (2019) did not report midspan cracks, the numerical models show some damage at the midspan. This discrepancy may be attributed to the damage criterion of the Mazars damage model, which is governed by positive tensile strain and is, therefore, sensitive to tensile

damage at the bottom of the midspan. Moreover, some oblique damage distributions are observed close to the opening zones in Fig. 21, which resemble the oblique cracks observed in the same positions in the experimental beam shown in Fig. 20.

Implementing the NDK approach results in slight variances in damage distributions for NDK models compared to refined CW models, as shown in Fig. 21. Considering that the web openings are large relative to the whole length of the beam, the damage is evident across most beam regions. Thus, the potential for model improvement is limited, and the NDK model used likely represents the optimal approach for capturing the damage distribution of this beam.

Reinforced Concrete Frame

The last example involves a full-scale RC frame to assess the capability of the proposed approach in practical engineering scenarios. The experimental campaign, reported in Baghi et al. (2018), consisted of three loading phases designed to explore the influence of infill wall on the behavior of an RC frame subjected to a column failure. The initial phase involved elastic loading of the RC frame without infill walls, followed by a second phase where the frame infilled with brick walls was loaded until the failure of brick walls. This study specifically considers the third phase, where the infilled wall was removed, and the bare frame was loaded until failure. The RC frame was designed to have strong columns and weak beams according to CEN (2005). Since the frame was overdesigned and no plastic strains were observed in the longitudinal reinforcement during the first two loading phases, it was assumed to be as new before the third loading phase. The height and width of this frame are around 2.55 and 5 m, respectively. Fig. 22 depicts the geometry and reinforcement details. A displacement-control method with a maximum value of 150 mm is used. The material properties are listed in Table 7.

The structural discretization is detailed in Fig. 23, where beam elements extend along the beam and columns. The black nodes indicating beam element nodes in Fig. 23(a) are only for illustrative purposes and do not represent their precise locations for calculation. The steel reinforcement within the concrete has been simplified into a square profile while maintaining the same cross-sectional area as its original circular form. This modification not only simplifies the process of cross-sectional discretization but also reduces computational demands. Four distinct cross-sectional discretizations are depicted in Fig. 23(b) to account for the inclusion of stirrups and the longitudinal rebars from the beam extending into the column. The discretization on the beam cross section is designed based on the assignment of beam elements along the

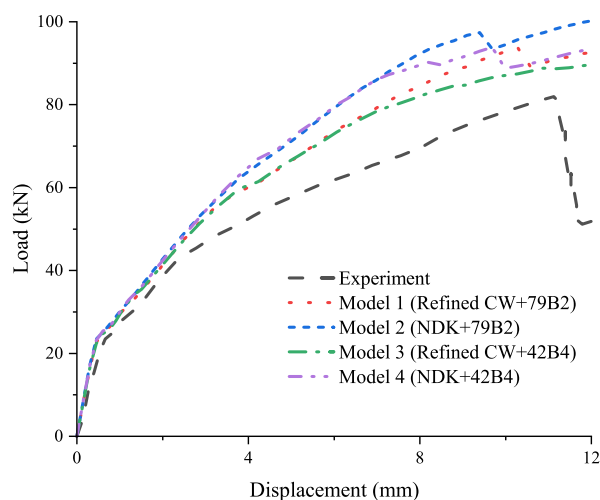


Fig. 19. Load-displacement curves for RC beam with web openings.

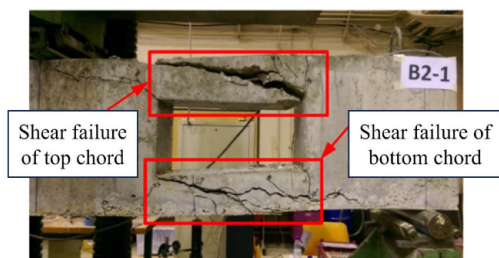


Fig. 20. Failures observed from experiments (Elsanadedy et al. 2019).

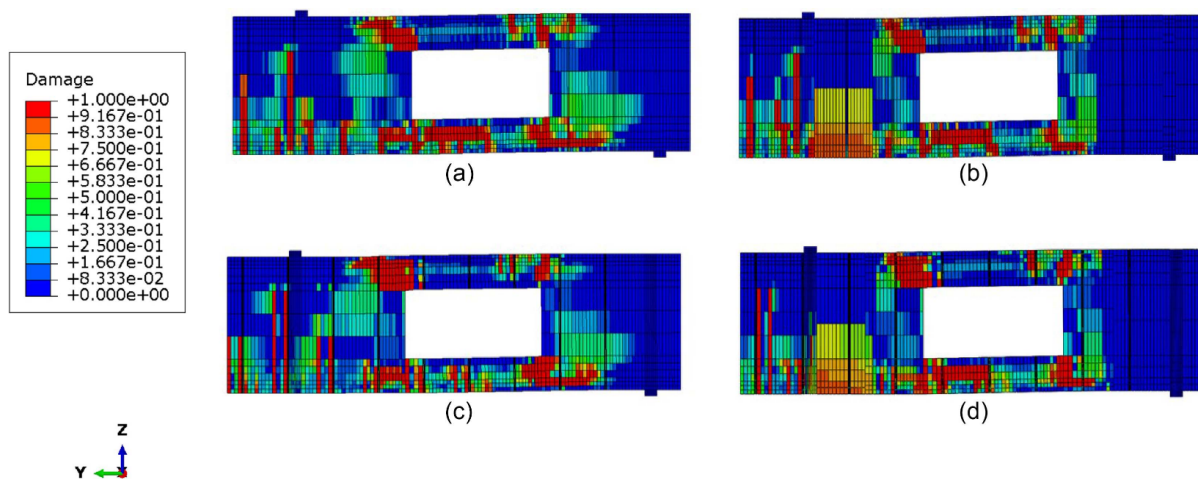


Fig. 21. Damage distributions of the RC beam with web openings from: (a) Model 1 (refined CW + 79B2); (b) Model 2 (NDK + 79B2); (c) Model 3 (refined CW + 42B4); and (d) Model 4 (NDK + 42B4) at the displacement of 11 mm.

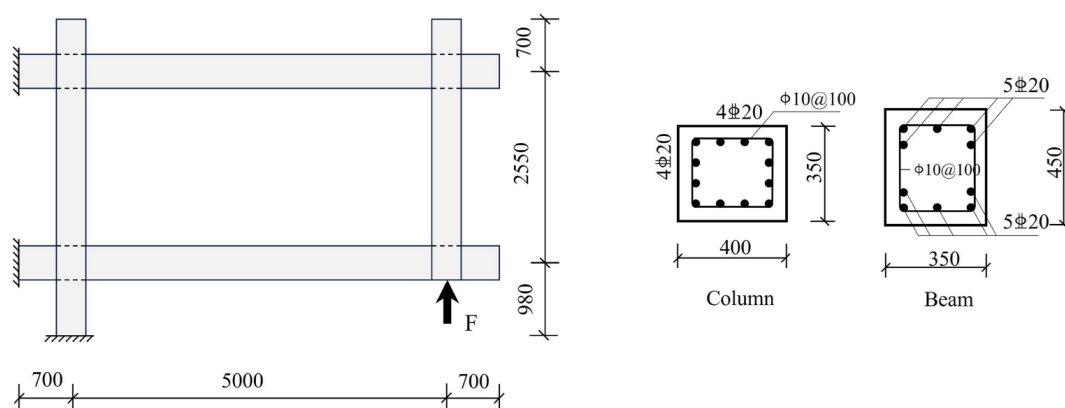


Fig. 22. Load layout and geometry of the studied RC frame (unit: mm).

Table 7. Material properties of the RC frame

Material	E (GPa)	f_{ctm} (MPa)	f_{cm} (MPa)	G_R (N/m)	G_{fc} (N/m)	ν	f_y (MPa)	f_{yu} (MPa)
Concrete	36.858	2.7	43	144.0	22,000	0.2	—	—
Steel	200	—	—	—	—	0.3	618	720

column, enabling node sharing at the beam–column junction. This design can ensure the displacement continuity at the beam–column connection, especially accounting for the horizontal extension of steel rebars from the beam into the column.

In total, 416 beam elements are required for the entire structure due to the periodic placement of stirrups. Four models, detailed in Table 8, are investigated with identical discretizations. However, Model 3 and Model 4 use quadratic beam elements, and Model 1 and Model 2 adopt linear beam elements. Model 2 and Model 4 apply the NDK approach as depicted in Fig. 24(b). LEs are mainly used for nodes at beam–column connections, and nodes in the remaining middle sections are defined using linear TE. Moreover, an ABAQUS model is also considered for comparison in which C3D8 solid elements are used for concrete, and B31 beam elements are adopted for steel. The approximate element size is 40 mm, and 200,598 DOFs are required for this ABAQUS model. Meanwhile, the same modified Mazars damage

model is implemented for the ABAQUS model through the UMAT subroutine.

The load–deflection diagrams of this RC frame from different numerical models are presented in Fig. 25, in which experimental and numerical results from Baghi et al. (2018) are included for comparison. All numerical models exhibit apparent deviations in initial stiffness compared to experimental results. However, all numerical models show similar initial stiffness. The discrepancy may be attributed to the formulation of microcracks at the top and bottom beams when the frame was tested in the first phase (Baghi et al. 2018).

Subsequently, the models using modified Mazars damage models in this work, including CUF models and the ABAQUS model, show slight divergences in the crack load compared to the OpenSees model from Baghi et al. (2018), which can be attributed to the use of different models. Afterward, all numerical models gradually match the experimental results around the period of steel yielding,

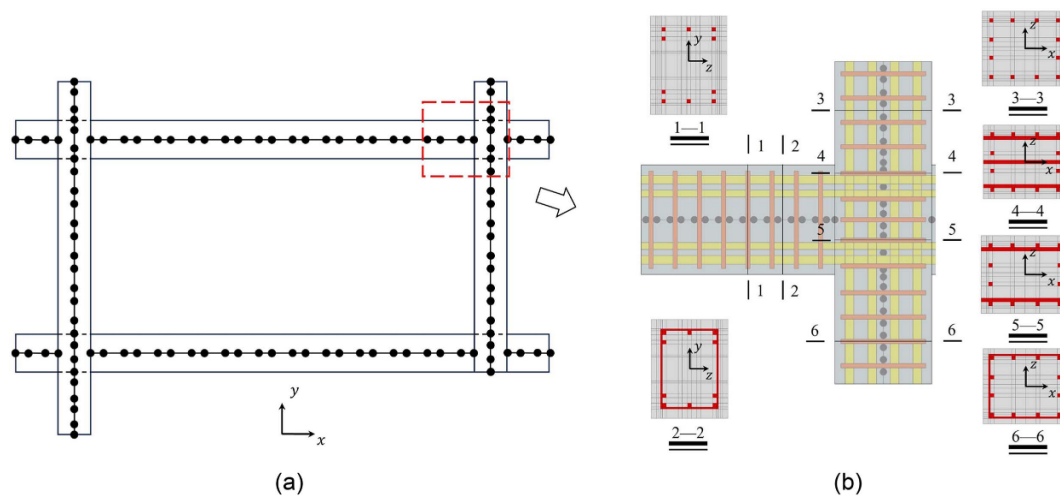


Fig. 23. (a) FE discretization of beam elements; and (b) cross-sectional discretization for the RC frame.

Table 8. Model information of the RC frame

Model number	Model 1	Model 2	Model 3	Model 4
Model type	Refined CW	NDK	Refined CW	NDK
Beam order	Linear (B2)	Linear (B2)	Quadratic (B3)	Quadratic (B3)
DoFs	328,968	189,684	1,029,240	545,076

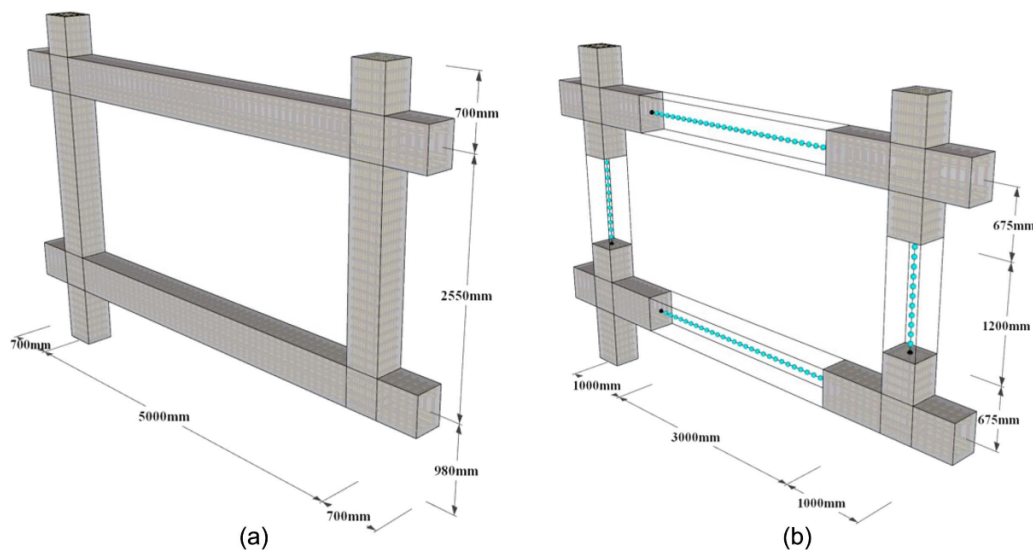


Fig. 24. (a) Refined CW model; and (b) NDK model for the analysis of the RC frame.

when the structural stiffness is further reduced, and the load-displacement curve begins to flatten. In general, the proximity of the CUF models to the ABAQUS and OpenSees models throughout the entire loading process and their alignment with the experimental results in the latter part of the loading process indicates their accuracy.

Minor discrepancies are also observed among different CUF models in Fig. 25. Model 1 and Model 2, which use the linear beam elements, demonstrate slightly lower curves than Model 3 and Model 4, which adopt the quadratic beam elements. These slight

deviations can be attributed to the fact that the characteristic element length might be underestimated for quadratic beam elements, as reported in Shen et al. (2024), thus leading to a slightly higher dissipated fracture energy than linear beam elements. Although this sensitivity to element order presents a challenge, the dependency on mesh size can be mitigated through the method from Shen et al. (2024). Moreover, Model 2 and Model 4 show marginally higher curves than Model 1 and Model 3, respectively. These observations are consistent with the findings from prior examples due to the lower-order kinematics used in NDK models.

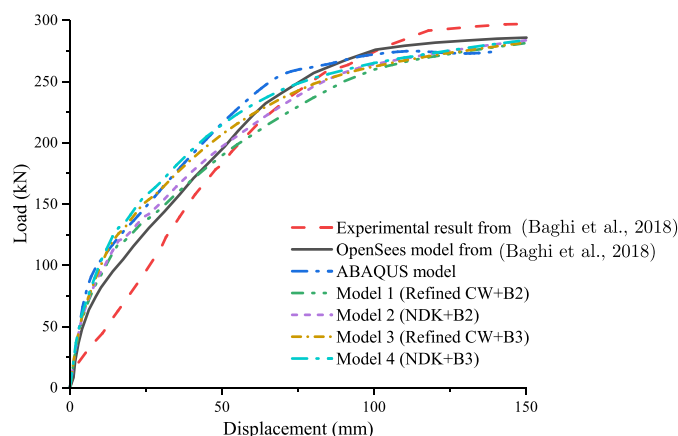


Fig. 25. Load–displacement curves for the RC frame.

It was reported that the experimental failure of this bare frame was governed by the formation of plastic hinges from Baghi et al. (2018), allowing for plastic rotation of beams at these critical connection points. Fig. 26 depicts the deformation and damage distribution patterns of four CUF models subjected to a displacement of 140 mm, demonstrating similar plastic rotation of beams along their ends.

As experimental cracks were not documented in Baghi et al. (2018), the corresponding damage distribution of the ABAQUS model, depicted as Fig. 26(e), is presented as a reference. Damage in beams from Model 1 and Model 2 is continuous and uniform, whereas the ABAQUS model exhibits periodically spaced strip damage. This discrepancy arises from differences in element size between the models. The beam element length in the CUF models for unconfined concrete is approximately 100 mm, while the element size in the ABAQUS model is around 40 mm. Models 3 and 4 with quadratic beam elements display strip damage distributions

in the beams similar to those observed in the ABAQUS model. The distinction between Models 1 and 3 is attributed to the different orders of beam elements. In continuum damage models, strain-softening behavior resulting from damage tends to be uniform across the entire linear beam element. In contrast, only part of the quadratic beam element undergoes strain-softening, while the remainder experiences unloading, as reported in Jirásek and Bauer (2012).

A minor discrepancy in damage distribution in the middle span of beams between Models 3 and 4 can be observed, attributed to the use of different expansion functions. This phenomenon has similarly been reported in previous comparisons between refined CW and NDK models. Overall, the damage distributions of CUF models align with those from the ABAQUS model, enhancing the accuracy of the proposed method in this work.

Regarding computational costs, Model 1 with linear elements requires more DoFs than the ABAQUS model due to the different numerical approaches utilized for reinforcements. Model 1 adopts CUF models that accurately represent the actual geometry of steel components, whereas the ABAQUS model simplifies these components as 1D beam elements. Adopting similar simplifications or lower-order models for steel components may offer further reductions in DoFs, enhancing the efficiency of CUF models in future developments. Nonetheless, incorporating the NDK approach saves significant computational resources, enabling Model 2 to achieve a 42.3% reduction in DoFs compared to Model 1. In addition, the DoFs needed for Model 2 are about 5% lower than those required by the ABAQUS model. While this 5% reduction may appear modest, the CUF models offer the additional advantage of providing a realistic 3D stress distribution of steel components, enhancing the models' high fidelity. Models 3 and 4 demand a considerable number of DoFs due to the use of higher-order beam elements. However, applying the NDK approach in Model 4 results in approximately a 47% saving in DoFs compared to Model 3. This

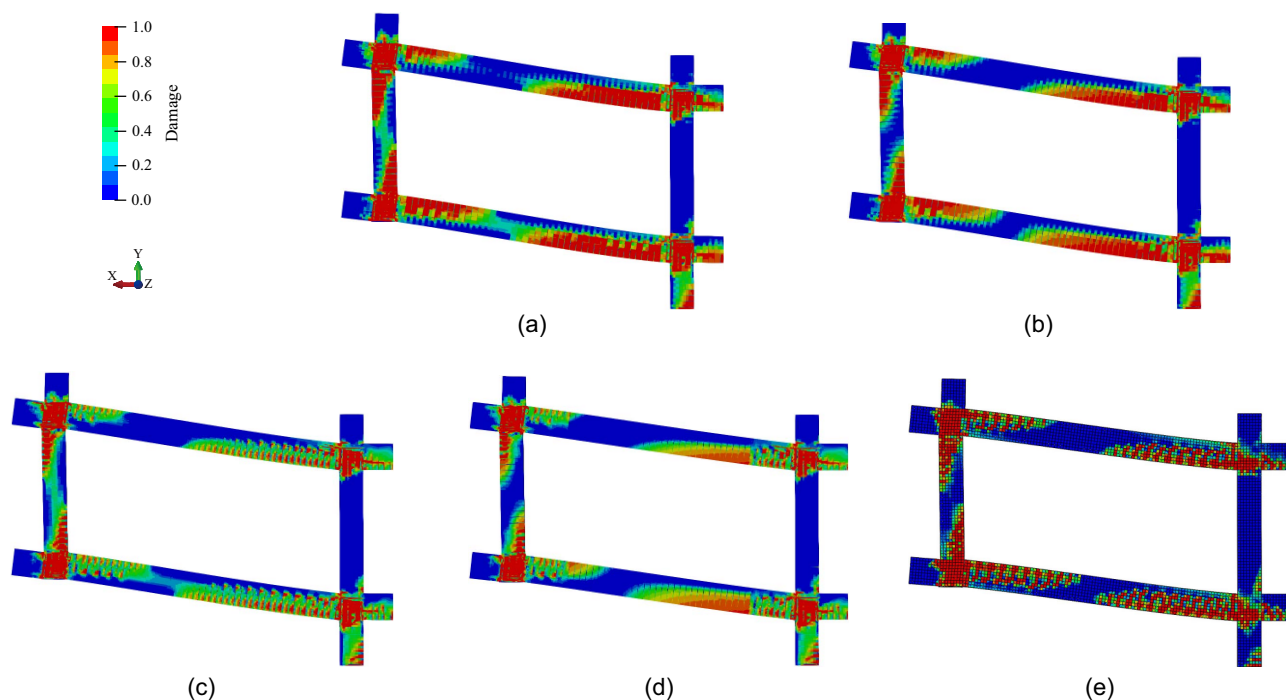


Fig. 26. Damage distributions of the RC frame from: (a) Model 1 (refined CW + B2); (b) Model 2 (NDK TE1 + B2); (c) Model 3 (refined CW + B3); (d) Model 4 (NDK TE1 + B3); and (e) ABAQUS model at the displacement of 140 mm (scale factor is 5).

reduction is significant given the large baseline number of DoFs required by higher-order models.

Conclusions

This study presents an NDK approach for 3D global–local damage analysis of RC structures, utilizing CUF-based advanced beam models. This approach allows for the application of different kinematic models at each node of the beam element. Specifically, enhanced models can be generated in critical areas using Lagrange polynomials in a CW manner. At the same time, lower-order refinement can be used for the remaining regions using Taylor polynomials. For the validation of the proposed NDK models, four complex RC structures from existing literature were selected. A modified Mazars damage model for concrete and von Mises plasticity for steel were applied to these numerical examples. The numerical results have been compared with reference results from the literature, yielding several meaningful conclusions:

1. The NDK approach optimizes beam models by combining the accuracy of local enhancement models with the efficiency of global models, maintaining displacement continuity without special coupling methods.
2. The refined CW model can accurately capture the damage behavior in RC structures, even in complex scenarios such as structures with web openings or full-frame designs. The NDK model demonstrates comparable performance.
3. Regarding computational resources, the NDK models reduce the DoFs by approximately 35%–60% compared to the refined CW model in earlier simple cases, signifying a substantial increase in computational efficiency. Notably, when the NDK models are applied to the larger engineering structures, a further significant reduction in computational costs is anticipated.
4. The strong scalability of the NDK models can ensure the realization of diverse NDK models by adjusting the cross-sectional kinematics at the beam element nodes as needed without additional mesh discretization.

Reducing the refined areas in the NDK model can save computational costs at the expense of model accuracy. However, defining these refined areas requires prior knowledge. Excessively large refined regions can lead to insufficient savings in computing resources, whereas refined areas that are too small will result in reduced model accuracy. Therefore, future work will aim to find an automatic model optimization strategy based on the proposed NDK approach. Furthermore, simplifying the representation of stirrups can decrease the total number of required beam elements, enabling constructing a model with computational demands similar to those of widely used fiber models.

Data Availability Statement

Some or all data, models, or code that support the findings of this study are available from the corresponding author upon reasonable request.

Acknowledgments

The authors are thankful for the support provided by the research projects 0305/1102/24160 MESTR—Modelação do Comportamento Estrutural and 0302/1102/24163 SEPINO—Sistemas Estruturais e Produtos Inovadores from LNEC.

References

- Arruda, M., J. Pacheco, L. M. Castro, and E. Julio. 2022. “A modified Mazars damage model with energy regularization.” *Eng. Fract. Mech.* 259 (Jan): 108129. <https://doi.org/10.1016/j.engfracmech.2021.108129>.
- Augello, R., E. Carrera, A. Pagani, M. Arruda, and J. Shen. 2023. “Node-dependent kinematic models applied to reinforced concrete structures.” *Math. Mech. Complex Syst.* 11 (1): 19–43. <https://doi.org/10.2140/memocs.2023.11.19>.
- Babazadeh, A., R. Burgueno, and P. F. Silva. 2015. “Use of 3D finite-element models for predicting intermediate damage limit states in RC bridge columns.” *J. Struct. Eng.* 141 (10): 04015012. [https://doi.org/10.1061/\(ASCE\)ST.1943-541X.0001253](https://doi.org/10.1061/(ASCE)ST.1943-541X.0001253).
- Baghi, H., A. Oliveira, J. Valença, E. Cavaco, L. Neves, and E. Júlio. 2018. “Behavior of reinforced concrete frame with masonry infill wall subjected to vertical load.” *Eng. Struct.* 171 (Sep): 476–487. <https://doi.org/10.1016/j.engstruct.2018.06.001>.
- Carrera, E., R. Augello, A. Pagani, and X. Xu. 2022. “Component-wise approach to reinforced concrete structures.” *Mech. Adv. Mater. Struct.* 29 (25): 3871–3888. <https://doi.org/10.1080/15376494.2021.1912442>.
- Carrera, E., G. Fiordilino, M. Nagaraj, A. Pagani, and M. Montemurro. 2019. “A global/local approach based on CUF for the accurate and efficient analysis of metallic and composite structures.” *Eng. Struct.* 188 (Jun): 188–201. <https://doi.org/10.1016/j.engstruct.2019.03.016>.
- Carrera, E., G. Giunta, and M. Petrolo. 2011. *Beam structures: Classical and advanced theories*. Chichester, UK: Wiley.
- Carrera, E., M. Petrolo, M. Cinefra, and E. Zappino. 2014. *Finite element analysis of structures through unified formulation*. Chichester, UK: Wiley.
- Carrera, E., and E. Zappino. 2017. “One-dimensional finite element formulation with node-dependent kinematics.” *Comput. Struct.* 192 (Nov): 114–125. <https://doi.org/10.1016/j.compstruc.2017.07.008>.
- Carrera, E., E. Zappino, and G. Li. 2018. “Finite element models with node-dependent kinematics for the analysis of composite beam structures.” *Composites, Part B* 132 (Jan): 35–48. <https://doi.org/10.1016/j.compositesb.2017.08.008>.
- Casanova, A., L. Jason, and L. Davenne. 2012. “Bond slip model for the simulation of reinforced concrete structures.” *Eng. Struct.* 39 (Jun): 66–78. <https://doi.org/10.1016/j.engstruct.2012.02.007>.
- CEN (European Committee for Standardization). 2005. *Eurocode 2: Design of concrete structures: Part 1-1: General rules and rules for buildings*. EN 1992-1-1. Brussels, Belgium: CEN.
- Ceresa, P., L. Petrini, and R. Pinho. 2007. “Flexure-shear fiber beam-column elements for modeling frame structures under seismic loading—state of the art.” *J. Earthquake Eng.* 11 (S1): 46–88. <https://doi.org/10.1080/13632460701280237>.
- Ceresa, P., L. Petrini, R. Pinho, and R. Sousa. 2009. “A fibre flexure–shear model for seismic analysis of RC-framed structures.” *Earthquake Eng. Struct. Dyn.* 38 (5): 565–586. <https://doi.org/10.1002/eqe.894>.
- Cheng, J., and P. B. Shing. 2022. “A beam-column element for modeling nonlinear flexural and shear behaviors of reinforced masonry walls.” *Earthquake Eng. Struct. Dyn.* 51 (8): 1918–1942. <https://doi.org/10.1002/eqe.3645>.
- D’Ambrisi, A., and F. C. Filippou. 1999. “Modeling of cyclic shear behavior in RC members.” *J. Struct. Eng.* 125 (10): 1143–1150. [https://doi.org/10.1061/\(ASCE\)0733-9445\(1999\)125:10\(1143\)](https://doi.org/10.1061/(ASCE)0733-9445(1999)125:10(1143)).
- de Souza Neto, E. A., D. Peric, and D. R. Owen. 2011. *Computational methods for plasticity: Theory and applications*. Chichester, UK: Wiley.
- Earij, A., G. Alfano, K. Cashell, and X. Zhou. 2017. “Nonlinear three-dimensional finite–element modelling of reinforced–concrete beams: Computational challenges and experimental validation.” *Eng. Fail. Anal.* 82 (Dec): 92–115. <https://doi.org/10.1016/j.engfailanal.2017.08.025>.
- Elsanadedy, H. M., Y. A. Al-Salloum, T. H. Almusallam, A. O. Alshenawy, and H. Abbas. 2019. “Experimental and numerical study on FRP-upgraded RC beams with large rectangular web openings in shear zones.” *Constr. Build. Mater.* 194 (Jan): 322–343. <https://doi.org/10.1016/j.conbuildmat.2018.10.238>.
- Feng, D.-C., G. Wu, Z.-Y. Sun, and J.-G. Xu. 2017. “A flexure-shear Timoshenko fiber beam element based on softened damage-plasticity

- model." *Eng. Struct.* 140 (Jun): 483–497. <https://doi.org/10.1016/j.engstruct.2017.02.066>.
- fib Special Activity Group. 2013. *fib model code for concrete structures 2010*. Berlin: Ernst & Sohn, Wiley.
- Firno, J. 2015. "Fire behaviour of reinforced concrete structures strengthened with CFRP strips." Ph.D. thesis, Instituto Superior Tecnico, Universidade de Lisboa.
- Firno, J., M. Arruda, J. Correia, and I. Rosa. 2018. "Three-dimensional finite element modelling of the fire behaviour of insulated RC beams strengthened with EBR and NSM CFRP strips." *Compos. Struct.* 183 (Jan): 124–136. <https://doi.org/10.1016/j.compstruct.2017.01.082>.
- Girgin, S. C., M. Moharrami, and I. Koutromanos. 2018. "Nonlinear beam-based modeling of RC columns including the effect of reinforcing-bar buckling and rupture." *Earthquake Spectra* 34 (3): 1289–1309. <https://doi.org/10.1193/063017EQS136M>.
- Halm, D., and A. Dragon. 1996. "A model of anisotropic damage by mesocrack growth; unilateral effect." *Int. J. Damage Mech.* 5 (4): 384–402. <https://doi.org/10.1177/105678959600500403>.
- Jirásek, M., and M. Bauer. 2012. "Numerical aspects of the crack band approach." *Comput. Struct.* 110 (Nov): 60–78. <https://doi.org/10.1016/j.compstruct.2012.06.006>.
- Kadhim, M. M., A. R. Jawdhari, M. J. Altaee, and A. H. Adheem. 2020. "Finite element modelling and parametric analysis of FRP strengthened RC beams under impact load." *J. Build. Eng.* 32 (Nov): 101526. <https://doi.org/10.1016/j.jobe.2020.101526>.
- Kaleel, I., M. Petrolo, and E. Carrera. 2018. "Elastoplastic and progressive failure analysis of fiber-reinforced composites via an efficient nonlinear microscale model." *Aerotecnica Missili Spazio* 97 (2): 103–110. <https://doi.org/10.1007/BF03405805>.
- MacGregor, J. G., J. K. Wight, S. Teng, and P. Irawan. 1997. Vol. 3 of *Reinforced concrete: Mechanics and design*. Upper Saddle River, NJ: Prentice Hall.
- Maekawa, K., H. Okamura, and A. Pimanmas. 2003. *Non-linear mechanics of reinforced concrete*. Boca Raton, FL: CRC Press.
- Marini, A., and E. Spacone. 2006. "Analysis of reinforced concrete elements including shear effects." *ACI Struct. J.* 103 (5): 645–655.
- Mazars, J. 1984. "Application de la mécanique de l'endommagement au comportement non linéaire et à la rupture du béton de structure." Ph.D. thesis, Laboratoire de Mécanique et Technologie, Université Pierre et Marie Curie Paris.
- Mullapudi, T., and A. Ayoub. 2013. "Analysis of reinforced concrete columns subjected to combined axial, flexure, shear, and torsional loads." *J. Struct. Eng.* 139 (4): 561–573. [https://doi.org/10.1061/\(ASCE\)ST.1943-541X.0000680](https://doi.org/10.1061/(ASCE)ST.1943-541X.0000680).
- Murcia-Delso, J., and P. Benson Shing. 2015. "Bond-slip model for detailed finite-element analysis of reinforced concrete structures." *J. Struct. Eng.* 141 (4): 04014125. [https://doi.org/10.1061/\(ASCE\)ST.1943-541X.0001070](https://doi.org/10.1061/(ASCE)ST.1943-541X.0001070).
- Nagaraj, M., E. Carrera, and M. Petrolo. 2023. "A global–local approach to the high-fidelity impact analysis of composite structures based on node-dependent kinematics." *Compos. Struct.* 304 (Jan): 116307. <https://doi.org/10.1016/j.compstruct.2022.116307>.
- Nagaraj, M., I. Kaleel, E. Carrera, and M. Petrolo. 2022. "Elastoplastic micromechanical analysis of fiber-reinforced composites with defects." *Aerotecnica Missili & Spazio* 101: 1–7. <https://doi.org/10.1007/s42496-021-00103-4>.
- Nagaraj, M., and M. Maiaru. 2023. "Progressive damage analysis of steel-reinforced concrete beams using higher-order 1D finite elements." *Int. J. Multiscale Comput. Eng.* 21 (4): 57–65. <https://doi.org/10.1615/IntJMultCompEng.2022045649>.
- Neuenhofer, A., and F. C. Filippou. 1997. "Evaluation of nonlinear frame finite-element models." *J. Struct. Eng.* 123 (7): 958–966. [https://doi.org/10.1061/\(ASCE\)0733-9445\(1997\)123:7\(958\)](https://doi.org/10.1061/(ASCE)0733-9445(1997)123:7(958)).
- Ogura, N., J. E. Bolander, and T. Ichinose. 2008. "Analysis of bond splitting failure of deformed bars within structural concrete." *Eng. Struct.* 30 (2): 428–435. <https://doi.org/10.1016/j.engstruct.2007.04.004>.
- Ouyang, C., E. Wollrab, S. Kulkarni, and S. Shah. 1997. "Prediction of cracking response of reinforced concrete tensile members." *J. Struct. Eng.* 123 (1): 70–78. [https://doi.org/10.1061/\(ASCE\)0733-9445\(1997\)123:1\(70\)](https://doi.org/10.1061/(ASCE)0733-9445(1997)123:1(70)).
- Petrangeli, M., P. E. Pinto, and V. Ciampi. 1999. "Fiber element for cyclic bending and shear of RC structures. I: Theory." *J. Eng. Mech.* 125 (9): 994–1001. [https://doi.org/10.1061/\(ASCE\)0733-9399\(1999\)125:9\(994\)](https://doi.org/10.1061/(ASCE)0733-9399(1999)125:9(994)).
- Saritas, A., and F. C. Filippou. 2009. "Numerical integration of a class of 3D plastic-damage concrete models and condensation of 3D stress–strain relations for use in beam finite elements." *Eng. Struct.* 31 (10): 2327–2336. <https://doi.org/10.1016/j.engstruct.2009.05.005>.
- Saritas, A., and F. C. Filippou. 2013. "Analysis of RC walls with a mixed formulation frame finite element." *Comput. Concr.* 12 (4): 519–536. <https://doi.org/10.12989/cac.2013.12.4.519>.
- Scano, D., E. Carrera, and M. Petrolo. 2023. "Use of the 3D equilibrium equations in the free-edge analyses for laminated structures with the variable kinematics approach." *Aerotecnica Missili & Spazio* 103: 1–17. <https://doi.org/10.1007/s42496-023-00177-2>.
- Shen, J., M. Arruda, A. Pagani, and E. Carrera. 2023a. "A regularized higher-order beam elements for damage analysis of reinforced concrete beams." *Mech. Adv. Mater. Struct.* 31 (1): 1–13. <https://doi.org/10.1080/15376494.2023.2245825>.
- Shen, J., M. T. Arruda, and A. Pagani. 2023b. "Concrete damage analysis based on higher-order beam theories using fracture energy regularization." *Mech. Adv. Mater. Struct.* 30 (22): 4582–4596. <https://doi.org/10.1080/15376494.2022.2098430>.
- Shen, J., A. Pagani, M. Arruda, and E. Carrera. 2022. "Exact component-wise solutions for 3D free vibration and stress analysis of hybrid steel–concrete composite beams." *Thin Walled Struct.* 174 (May): 109094. <https://doi.org/10.1016/j.tws.2022.109094>.
- Shen, J., M. R. Tiago Arruda, and A. Pagani. 2024. "A consistent crack bandwidth for higher-order beam theories: Application to concrete." *Int. J. Damage Mech.* 33 (4): 269–292. <https://doi.org/10.1177/10567895231215557>.
- Sinaei, H., M. Shariati, A. H. Abna, M. Aghaei, and A. Shariati. 2012. "Evaluation of reinforced concrete beam behaviour using finite element analysis by ABAQUS." *Sci. Res. Essays* 7 (21): 2002–2009. <https://doi.org/10.5897/SRE11.1393>.
- Spacone, E., F. C. Filippou, and F. F. Taucer. 1996. "Fibre beam–column model for non-linear analysis of R/C frames: Part I. Formulation." *Earthquake Eng. Struct. Dyn.* 25 (7): 711–725. [https://doi.org/10.1002/\(SICI\)1096-9845\(199607\)25:7<711::AID-EQE576>3.0.CO;2-9](https://doi.org/10.1002/(SICI)1096-9845(199607)25:7<711::AID-EQE576>3.0.CO;2-9).
- Taucer, F., E. Spacone, and F. C. Filippou. 1991. Vol. 91 of *A fiber beam-column element for seismic response analysis of reinforced concrete structures*. Berkeley, CA: Earthquake Engineering Research Center, College of Engineering, Univ. of California, Berkeley.
- Urmson, C. R., and J. B. Mander. 2012. "Local buckling analysis of longitudinal reinforcing bars." *J. Struct. Eng.* 138 (1): 62–71. [https://doi.org/10.1061/\(ASCE\)ST.1943-541X.0000414](https://doi.org/10.1061/(ASCE)ST.1943-541X.0000414).